

# Evaluation the cytotoxic/viability effect of gelatin/bioactive glass conduits by MTT assay

Masoumeh Foroutan Koudehi<sup>1</sup>, Kamali Mahdi<sup>3</sup>, Nourani Mohammad Reza<sup>1</sup>, Abbas Ali Imani Fooladi<sup>2\*</sup>

1-Tissue Engineering Division, Applied Biotechnology Research Center, Baqiyatallah University of Medical Sciences, Tehran, Iran.

2-Applied Microbiology Research Center, Baqiyatallah University of Medical Sciences, Tehran, Iran.

3-Nano biotechnology Research Center, Baqiyatallah University of Medical Science.

Received: 5 September 2013 / Accepted: 15 February 2014

## Abstract:

Peripheral nerve injury can successfully heal, if an appropriate environment and route be provided. This study was designed to develop a novel gelatin/ bioactive glass conduits using freeze-drying technique. The gelatin/ bioactive glass conduits characterized using Fourier transform infrared spectroscopy (FTIR). The surface morphology of the Nanocomposites were investigated through scanning electron microscopy (SEM). Cytotoxicity Evaluation show that the CHO cells had attached and proliferated in the surroundings of the conduit. Biocompatibility was assessed by MTT (3-[4,5-dimethylthiazol-2-yl]-2,5-diphenylte-2H-tetrazolium bromide) assay which showed that gelatin/bioactive glass conduits had good cytocompatibility.

**Key Words:** bioactive glass, Conduit, Cytotoxicity effects, tissue engineering.

**Introduction** Peripheral nerves are exposed to physical injuries usually caused by trauma that may lead to a significant loss of sensory or motor functions and is considered as a serious health problem for societies today. This condition requires the use of nerve grafts and peripheral nerve substitutes to support the healing process. Autografts have been considered as the gold standard for peripheral nerve repair due to their obvious properties; however there are restrictions on autografts use such as limitations in availability of donor site, the sensation loss of donor area and donor site morbidity.

Conduits as a nerve growth structure have been developed to improve nerve gap regeneration. Tissue engineering, combining the biological knowledge, materials and the, is a contemporary approach to repair and rebuild the lost tissues and organs. Fabrication of porous gelatin scaffolds using a freeze-drying method is also an effective method, due to advantage of this technique.

Gelatin, is a partial derivative of collagen, and has a wide range of uses in the pharmaceutical food and cosmetic industries [1]. For applications as nerve tissue healing, gelatin was used as a polymer to increase the flexibility of the scaffold [2, 3]. However, it has a poor mechanical property [1, 4]. Bioceramics are often used in combination with biodegradable polymers to achieve the best possible mechanical and biological performance. The characteristic of bioactive glasses (BG) include; excellent bioactivity, ability to deliver cells, and controllable biodegradability [5]. These advantages make bioactive glasses a promising scaffold material for tissue engineering. In the present study, we investigated the suitability of a composite nerve conduit for peripheral nerve regeneration fabricated with bioglass and gelatin utilizing freeze drying technique.

## Materials and methods

### Conduits fabrication

\*Corresponding Authors: Nourani Mohammad Reza  
Tehran, Iran. Tel/Fax: 98-21-88211523, r.nourani@yahoo.com

At first a homogeneous aqueous solution of microbiology-grade Gelatin (GEL) (10% weight per volume, w/v) was prepared and BG Nanopowder was added to obtain a GEL (70)/BG (30) weight composition. After homogenization through stirring, special mandrels were dipped in solution several times. To produce porous structures, the mandrel was transferred to a freeze dryer at  $-57^{\circ}\text{C}$  and 0.05 mbar for 24 h in order to produce a 3D porous structure through sublimation to form a gelatin network matrix on the pore walls and the surface of conduits. The emerging conduits had the following dimensions: Internal diameter 1.6 mm. Next, nanocomposite was soaked in a cross-linking bath of glutaraldehyde (GA) solution of 0.5% (w/v) for 24 hours to reduce biodegradation and enhance the biomechanical properties (fig.1)



Fig.1 conduits after cross linking

#### Fourier Transforms Infrared Spectroscopy (FTIR)

The Fourier Transform Infrared Spectroscopy (FTIR) was operated in the mid-infrared range from  $400\text{--}4000\text{ cm}^{-1}$  in reflection mode. The FTIR spectrometer was used to characterize the presence of specific chemical groups in the functional groups of Nanocomposite conduits. For IR analysis, in first 1 mg of the powder samples were carefully mixed with 300 mg of KBr (infrared grade) and palletized under vacuum. Then the Pellets were analyzed at the scan speed of  $120\text{ scan min}^{-1}$  with  $4\text{ cm}^{-1}$  resolution.

#### Scanning electron microscopy (SEM)

Scanning electron microscope photomicrographs (SEM-Philips XL30) were used to measure the average pore size of the modeled conduits. The Nanocomposite samples were coated with gold using a (EMITECH K450X, England) Sputter before examination under scanning electron microscope that operated at the acceleration voltage of 15 kV. By using SEM, the pore size of the cross-section of the samples was observed.

#### Cell Seeding on conduit

gelatin/ bioactive glass conduits were sterilized by ethylene oxide at  $38^{\circ}\text{C}$  and 65% relative humidity for 8 hours. After 24 h aeration in order to remove the residual ethylene oxide, the conduits were placed inside a standard 24-well-plate and finally with culture medium. For cytotoxicity evaluation, culture in Dulbecco's Modified Eagle Medium

(DMEM) supplemented with 10% fetal bovine serum (FBS) and streptomycin/penicillin  $100\text{ U/mL}$  (1%). Chinese hamster ovary cells with a density of  $4 \times 10^5\text{ cell/mL}$  were added to the samples in PS plates and maintained in an incubator ( $37^{\circ}\text{C}$ ,  $\text{CO}_2$  5%) for 48 h<sup>[6]</sup>. The Nanocomposite conduits crosslinked with GA 0.5% (w/v) were studied for this reason. The samples were kept in 100% ethanol for 15 min, and then visualized by light microscopy (Nikon Eclipse 50i)[7].

#### MTT detection of viable cells

The viability and proliferation of layered BG conduits were determined by 3-(4,5-Dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) assay[28]. Cytotoxicity effects of conduits were investigated on Miapaca-2 cell lines (purchased from the Pasteur Institute, Iran). The cells were plated in 96-well culture plates at  $1.7 \times 10^4\text{ cell/well}$ . They were cultured in RPMI-1640 supplemented with 10% FBS and 1% PS in 5%  $\text{CO}_2$  at  $37^{\circ}\text{C}$ . After 72 h, mediums were removed and  $100\text{ }\mu\text{L}$  of fresh medium and  $13\text{ }\mu\text{L}$  of MTT solutions ( $5\text{ }\mu\text{g/mL}$ , diluted with RPMI 1640 without phenol red) were added to each well. Incubation was allowed for another 4 h in dark at  $37^{\circ}\text{C}$ . Mediums were removed and  $100\text{ }\mu\text{L/well}$  DMSO (dimethyl sulfoxide, Sigma, Aldrich, Germany) was added to dissolve formazan crystals. Wells were finally read at 540 nm on an ELISA plate reader (Tecan Sunrise TM) and percentage of viability calculated. The well without conduit was used as a negative control and cell viability was defined as 100% for the MTT assay control. Each test was repeated three times.

## Results

#### FTIR analysis

The BG conduits also represent the FTIR spectrum of the Nanocomposite that exhibited a number of new characteristic spectral bands, the most characteristics of which were protein spectrums such as: N-H bending vibration at  $1260\text{ cm}^{-1}$  for the amide III, N-H bending vibration at  $1560\text{ cm}^{-1}$  for the amide II, C=O stretching vibration at  $1670\text{ cm}^{-1}$  for the amide I, C-H bending vibration at  $2952\text{ cm}^{-1}$  for the amide B and band at  $3570\text{ cm}^{-1}$  indicating the presence of O-H groups, while the characteristic spectral bands for BG were present in the Spectrum for Nanocomposites well (Fig.2)

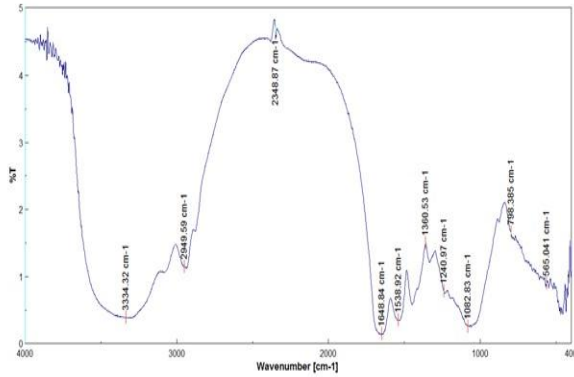


Fig.2FT-IR spectroscopy

**SEM observations**

The SEM micrograph images showed the porous structure of the conduit (Fig. 3).The sponge-like inner layer of conduits could permit the exchange of Feeding and fluids, and Ability a great space for the storage of the released Nerve growth.

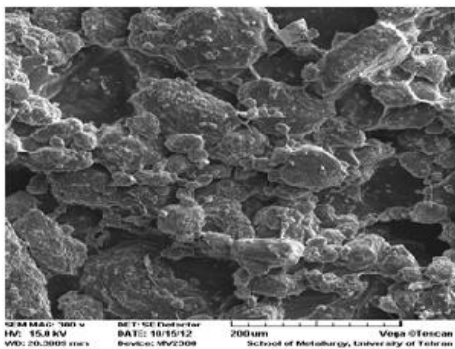


Fig3.SEM image of the porous nanocomposite conduit, inner layer of conduit wall (300x)

Figure 4 shows the pictures taken from seed cells on conduit specimens. The biocompatibility of the conduits, which was cross linked with 0.5 % GA, was assessed for cellular attachment, spreading and finally developing filopodias. After 3 days of culture, the CHO cells had attached and proliferated in the surroundings of the conduit

**MTT detection of viable cells**

MTT tests showed that the cell viability of Miapaca-2 cultured in the conduit extract was not significantly different from that in plain medium of cells during 72 h. This result clearly suggested that the fabricated conduits were nontoxic and posed as good candidates to be used as nerve conduits(Fig.5).

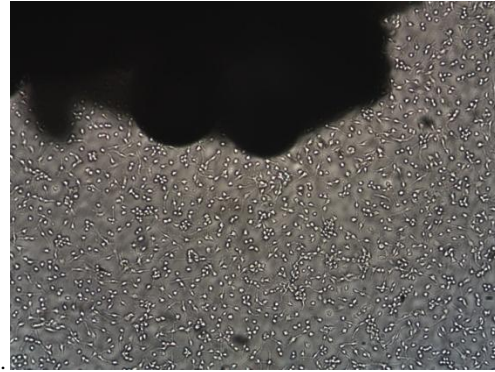


Fig4. Chinese hamster ovary cells cultured on the produced conduits cross linked with 0.5% GA.

The results obtained from the test and control after 72 h showed no significant cytotoxicity effects ( $P \leq 0.05$ ).

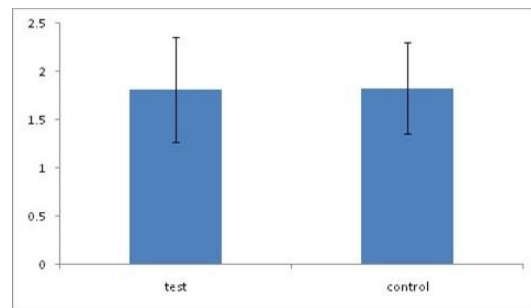


Fig.5MTT analysis results after 72 hours. Groups Test and control indicate disc and negative control Samples, respectively. No significant differences were observed between the two groups test group and control group.

**Discussion**

The gelatin/ bioactive glass conduits were prepared from a mixture of aqueous gelatin solution with Bioactive glass synthesized through the Sol/Gel method by freeze drying techniques as a bioactive Nanocomposite conduit.

FTIR microscopy has been proofed to be a powerful tool to characterize the presence of various chemical groups. In previous studies for gelatin and hydroxyapatite that the first one at about  $1,359 \text{ cm}^{-1}$  indicates the formation of the chemical bond between carboxyl groups from gelatin and  $\text{Ca}^{2+}$  ions from the BG[8, 9].The second bond at  $2.349 \text{ cm}^{-1}$  appeared after crosslinking of gelatin with GA as mentioned former by Azami, et al[8].

The SEM micrograph images showed the porous structure in the dense outer layer and the inner layer of the our conduit the is conforming with results SEM test Yumin Yang et al[10].

Our data obtained from MTT analysis showed no cytotoxic effects on viability and proliferation properties of cells during 72 hours. Son'ajantova' and Colleagues reported that the bioglass scaffold just a slight cytotoxicity and comfortable biocompatibility [11]. Therefore their data confirmed our data in this regard.

**Conclusions** According to our findings gelatin/ bioactive glass conduit, as a biocompatible novel biomaterial, could be a suitable candidate to be used for peripheral nerve regeneration.

#### Acknowledgments

The authors appreciate the Baqiyatallah University of Medical Sciences, Tehran, Iran for their financial support to perform this project.

#### References

1. Boedtke, H. and P. Doty, *A study of gelatin molecules aggregates and gels*, *J. Phys. Chem*, 1954: p. 968–983.
2. Rezwan, K., et al., *Biodegradable and bioactive porous polymer/inorganic composite scaffolds for bone tissue engineering*. *Biomaterials*, 2006. 27(18): p. 3413-31.
3. Guarino, V., F. Causa, and L. Ambrosio, *Bioactive scaffolds for bone and ligament tissue*. *Expert Rev Med Devices*, 2007. 4(3): p. 405-18.
4. Liu, X., et al., *Biomimetic nanofibrous gelatin/ apatite composite scaffolds for bone tissue engineering*. *Biomaterials*, 2009: p. 2252–2258.
5. Mozafari, M., et al., *Development of macroporous nanocomposite scaffolds of*

*gelatin/bioactive glass prepared through layer solvent casting combined with lamination technique for bone tissue engineering*. *Ceramics International* 2010: p. 2431-2439.

6. picot, J., *human cell culture protocol*. 2004, CA, USA
7. Fassina L, S.E., Visai L, Avanzini MA, Cusella De Angelis MG, Benazzo F, Van Vlierberghe S, Dubruel P, Magenes G., *Use of a gelatin cryogel as biomaterial scaffold in the differentiation process of human bone marrow stromal cells*. *Conf Proc IEEE Eng Med Biol Soc.*, 2010: p. 247-50.
8. Azami, M., F. Moztarzadeh, and M. Tahriri, *Preparation characterization and mechanical properties of controlled porous gelatin/hydroxyapatite nanocomposite through layer solvent casting combined with freeze-drying and lamination techniques*. *Porous Mater*, 2009.
9. Mortazavi, V., et al., *Antibacterial effects of sol-gel-derived bioactive glass nanoparticle on aerobic bacteria*. *Biomed Mater Res A*, 2010: p. 160-8.
10. Yang, Y., et al., *Nerve conduits based on immobilization of nerve growth factor onto modified chitosan by using genipin as a crosslinking agent*. *Pharmaceutics and Biopharmaceutics*, 2011: p. 519–525.
11. S, J., et al., *Biocompatibility and cytotoxicity of bioglass-ceramic composite with various P2O5 content in Li2O-StO2-CaO-CaF2-P2O5 system on fibroblast cell lines*. *Acta Chimica Slovaca*, 2011.