

# Synthesis of Cuprous Oxide Nano Cubes and Platelets Using Both Electrodes of Copper

DANIAL AHMAD\*, MUHAMMAD SOHAIL\*, FAYAZ HUSSAIN\*, HUMAIR SIDDIQUI\*, AND MUHAMMAD YASIR\*\*

RECEIVED ON 19.01.2018 ACCEPTED ON 25.05.2018

## ABSTRACT

Cu<sub>2</sub>O (Cuprous Oxide) is usually produced using expensive electrodes such as platinum, graphite, etc. In the present study, it is shown that Cu<sub>2</sub>O nanostructures can be synthesized by electrolysis using copper as both anode and cathode. In the present study, the effect of electrolyte pH on the morphology of the Cu<sub>2</sub>O nanostructures was studied. For this, the copper electrodes of 99.99% purity with 3x3x0.3 mm dimensions were dipped in the electrolytes of simple distilled and double distilled water and connected with the external power source. The synthesized products were analyzed using SEM (Scanning Electron Microscope), EDS (Energy Dispersive Spectroscopy) and UV spectroscopy. Results showed that Cu<sub>2</sub>O nanostructures of 67 and 150 nm size were developed when the pH of electrolyte was 6.4 and 5.7 respectively, otherwise not. From the course of experiments conducted in this work it is noted that pH play vital role in the production of Cu<sub>2</sub>O nanoparticles using simple electrolysis technique.

**Key Words:** Cuprous Oxide, Nano-Platelets, Nano-Cubes, Electrolysis, Scanning Electron Microscopy.

## 1. INTRODUCTION

Nanostructures such as nanowires and nanocubes attracts the considerable attention in recent years as they have a lot of superior electronic, electrochemical, catalytic and magnetic properties [1]. They have been utilized for different applications in microelectronics, solar energy, organic contaminants conversion, chemical industry, photovoltaic materials, gas sensors, biosensors, lithium ion batteries, nonmagnetic devices, semiconductors, and as well as in super conductors [2]. Despite to this, these materials can

also be used as a catalyst for water splitting under visible light [3-4]. Obviously, there are many advantages of Cu<sub>2</sub>O nanostructures too, to be used as a photo catalyst of low toxicity, environmentally friendly, a low cost electrode and easily available in abandoned quantity material [5-7]. Several methods have been reported to synthesize the Cu<sub>2</sub>O nanostructures, that is, electrodeposition/ electrolytic, sonochemical, PVD (Physical Vapor Deposition), thermal relaxation, liquid-phase reduction, the CPSA (Complex Precursor Surfactant-Assisted) Route

Authors E-Mail: (daniahmad92@hotmail.com, msohailhanif@neduet.edu.pk, fhussain@neduet.edu.pk, ahumair@hotmail.com, myasir@uok.edu.pk)

\* Department of Materials Engineering, NED University of Engineering & Technology, Karachi, Pakistan.

\*\* Department of Chemical Engineering, University of Karachi, Karachi, Pakistan.

and vacuum evaporation. All these approaches, usually employ a complex control over the process as well as they require the expensive materials/chemicals to fabricate Cu<sub>2</sub>O nanostructures [2,8].

In the application point of view, Cu<sub>2</sub>O is considered as a promising and effective p-type semiconductor ceramics, having direct bandgap of 2.1 eV [2,5-8], while the bandgap of 1.64 eV could be achieved if the hydrothermal electrochemical deposition technique was used to deposit thin films [9]. Further to this, hollow nanospheres with different outer diameters (100-200 nm) were fabricated by Chang et. al. [11], to claim that the respective band gap ( $E_g = 2.405-2.170$  eV) of different sizes with different colours respectively, of Cu<sub>2</sub>O were being discussed for the application of solar energy harvesting devices in the visible range. Rakhshani et. al. [12], reviewed and emphasized along with the size scale, the processing technique parameters also have the effect on the band gap of Cu<sub>2</sub>O. In general, it is noted that materials having nanoscale size, possessing quite different properties as compared to the microstructural materials. For instance, Cu<sub>2</sub>O nanostructures were also exhibited comparatively useful and enhanced optical and electronic properties, inverse to the bulk [1,11]. Cu<sub>2</sub>O nanoparticles can be stabilized by forming a thin layer of copper(II) oxide, also known as cupric oxide (CuO), on the surface of Cu<sub>2</sub>O. Pure Cu<sub>2</sub>O are not stable in bulk and does not show any passivity under ambient atmosphere and temperature. In contrast, it was worthwhile, the engineered nano size (around 25nm) of Cu<sub>2</sub>O was reported more stable than CuO [7-8]. Researchers have also synthesized and applied Cu<sub>2</sub>O nanostructure in combination with different materials such as aluminum, graphene, polymers, etc.[12-16].

Despite to use the cheap electrodes made of Cu metal, many workers have been produced Cu<sub>2</sub>O nanostructures by utilizing expensive electrodes of Pt and graphite as cathode [5,7]. In this work, the production of Cu<sub>2</sub>O nanostructures were obtained through the electrolysis process, where the Cu plates were used for both cathode and anode at the same time. In addition, the distilled water, with different pH values, was used to study the effect of the alkaline and acidic nature of the electrolyte (corrosive medium) on morphologies of nano-oxides (corrosive product) of Cu.

## **2. EXPERIMENTAL PROCEDURE**

### **2.1 Materials Used**

Copper (99.99% pure) plates were purchased and used after rough polishing with alumina (0.2 μm) containing suspension followed by intermediate polishing and thorough cleaning in analytical grade acetone. Distilled water of different pH values was obtained locally.

### **2.2 Synthesis of Cuprous Nanostructures**

In present work, the two pure Cu metal electrodes were placed parallel to each other into the electrolyte. In all experiments, Cu plates of the same dimensions were used, as mentioned in Table 1. Throughout the experiments, cathode to anode ratio was set to 1:1 and distance between them was 1 cm. Whereas, the pH and conductivity of the water used as an electrolyte is shown in Table 1.

The copper plates were supported and mounted vertically downward with the help of polymer lid as shown in Fig. 1. Than anode and cathode were connected to DC power supply by using copper wire (99.9% pure) and finally electrolysis experiments were conducted at different current and volts as shown in Table 2.

## 2.2 Characterization

The material deposited on either anode or cathode was analyzed using SEM (FEI Quanta 200), and UV-Visible spectrophotometer (22pc spectrum lab).

## 3. RESULTS AND DISCUSSION

Different nanostructures of  $\text{Cu}_2\text{O}$ , shown in Figs. 2-3, were formed during the course of electrolysis experiments. It can be seen in Figs. 2-3 that when pH value was less than 7, the mixed nanostructures containing nano-cubes and nano-platelets were developed. Analysis of SEM images indicated that dimensions of nano-plates and nano-cubes developed, below pH 7, was roughly 67-100 and 120-132 nm respectively.

In order to ensure that product collected at cathode and anode, when pH was less than and greater than 7, is copper, the EDS analysis and UV visible spectroscopy was carried out. The EDS analysis result shown in

Fig. 4 confirmed that product is mainly composed of copper. Similarly, the spectrum of UV visible spectroscope, shown in Fig. 5, further provided the supported evidences.



FIG. 1. EXPERIMENTAL SETUP

TABLE 1. ELECTRODE PLATE (COPPER) DIMENSIONS

Electrode Properties	Cathode Material		99.9% Copper	
	Anode Material		99.9% Copper	
	Electrode Dimensions (cm)		3x3x0.3	
	Electrode Surface Area ( $\text{cm}^2$ )		20.7	
Electrolyte Test Results	Water (Electrolyte)	Double Distilled	Single Distilled	Single Distilled
	pH	5.704	6.4	7.9
	Conductivity (Micro Siemens per cm)	1.6	16.8	98.7

TABLE 2. OPERATING CONDITION OF EXPERIMENT

Electrolyte			Operating Parameters		
Electrolyte	pH	Conductivity	I (amp)	V (volts)	Time (mins)
1	5.704	1.6	0.001	20	120
2	6.400	16.8	0.001	20	120
3	7.900	98.7	0.001	20	120

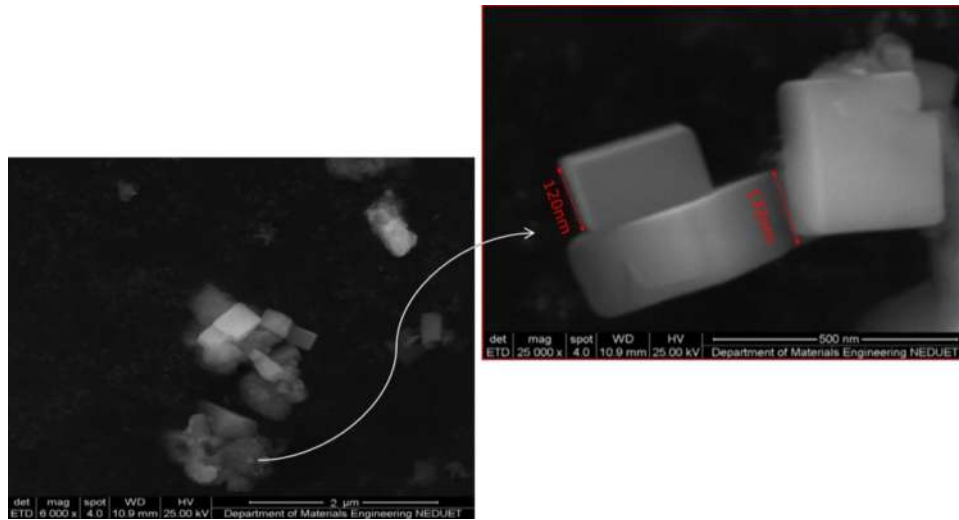


FIG. 2. SEM IMAGE OF NANO-COPPER PARTICLES OBTAINED AT pH 5.7

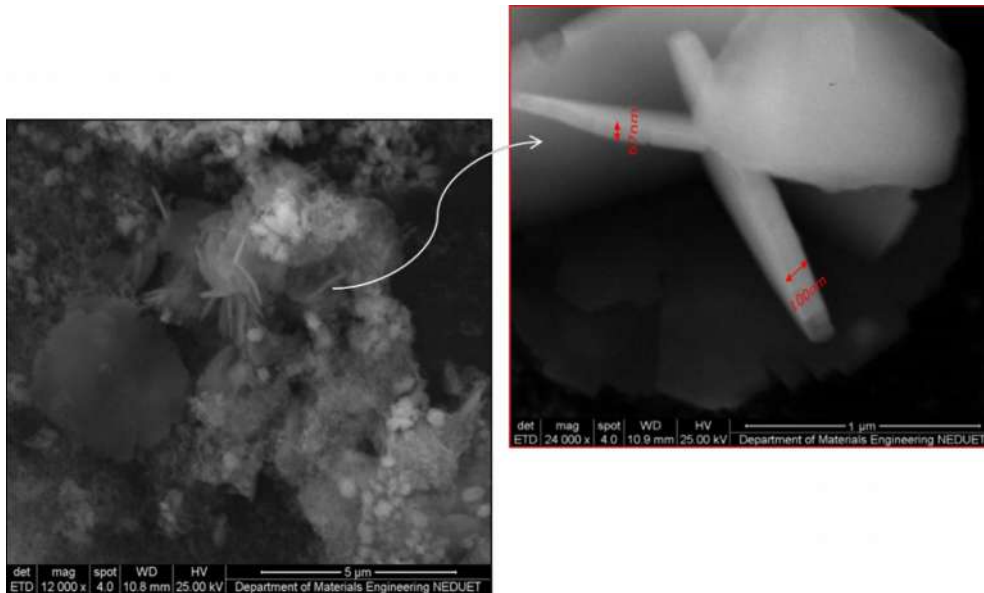


FIG. 3. SEM IMAGE OF NANO-COPPER PARTICLES OBTAINED AT pH 6.4

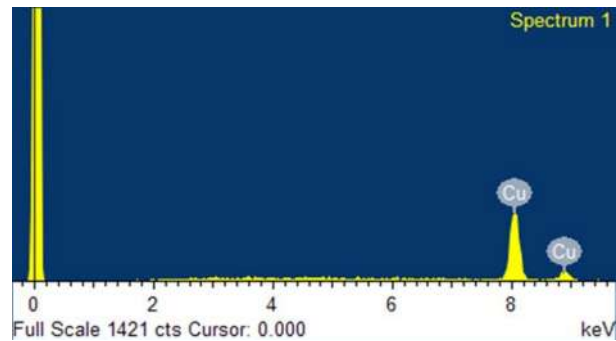


FIG. 4. ENERGY DISPERSIVE X-RAY SPECTRUM OF OBTAINED PRODUCT

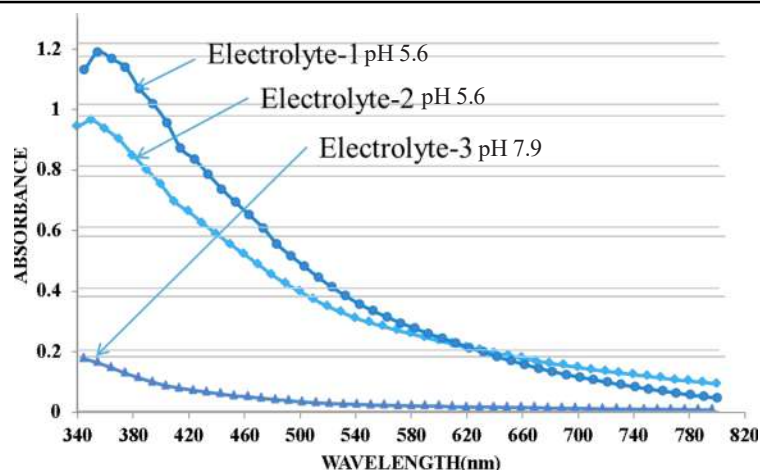


FIG. 5. UV ABSORBANCE OF PRODUCT OBTAINED AT THREE PH VALUES

## 5. CONCLUSION

Following are the main conclusions of the present work:

- (i) pH of the electrolyte plays vital role in the synthesis of the nano-copper plates.
- (ii) The shape and size are strongly dependent on the pH of the electrolyte
- (iii) Acidic conditions of electrolyte are optimal for synthesis of nano copper

## ACKNOWLEDGEMENT

The authors express immense thanks to the Faculty and Staff of the Department of Materials Engineering, NED University of Engineering & Technology, Karachi, Pakistan, for their support during the experimental work.

## REFERENCES

- [1] Cao, G., and Liu, D., "Template-Based Synthesis of Nanorod, Nanowire, and Nanotube Arrays", *Advances in Colloid and Interface Science*, Volume 136, Nos. 1-2, pp. 45-64, 2008.
- [2] Singh, D.P., Neti, N.R., Sinha, A.S.K., and Srivastava, O.N., "Growth of Different Nanostructures of  $\text{Cu}_2\text{O}$  (Nanowires, Nanowires, and Nanocubes) by Simple Electrolysis Based Oxidation of Copper", *The Journal of Physical Chemistry-C*, Volume 111, No. 4, pp. 1638-1645, 2007.
- [3] Hara, M., Komoda, M., Hasei, H., Yashima, M., Ikeda, S., Takata, T., Kondo, J.N., and Domen, K.A., "Study of Mechano-Catalysts for Overall Water Splitting", *The Journal of Physical Chemistry-B*, Volume 104, No. 4, pp. 780-785, 2000.
- [4] de Jongh, P.E., Vanmaekelbergh, D., and Kelly, J.J., " $\text{Cu}_2\text{O}$ : A Catalyst for the Photochemical Decomposition of Water", *Chemical Communications*, Volume 12, pp. 1069-1070, 1999.
- [5] Asano, Y., Nakaoka, K., Murashiro, K., Komatsu, T., and Hoshino, K.T., "Template-Free Electrochemical Preparation of Dendritic Copper Nanowire and Its Capacitor Properties", *Materials Letters*, Volume 81, pp. 162-164, 2012.
- [6] Huang, L., Peng, F., Yu, H., and Wang, H., "Preparation of Cuprous Oxides with Different Sizes and Their Behaviors of Adsorption, Visible-Light Driven Photocatalysis and Photocorrosion", *Solid State Sciences*, Volume 11, No. 1, pp. 129-138, 2009.

- [7] Shoeib, M.A., Abdelsalam, O.E., Khafagi, M.G., and Hammam, R.E., "Synthesis of Cu<sub>2</sub>O Nanocrystallites and Their Adsorption and Photocatalysis Behavior", *Advanced Powder Technology*, Volume 23, No. 3, pp. 298-304, 2012.
- [8] Ng, S., and Ngan, A., "One and Two-Dimensional Cuprous Oxide Nano/Microstructures Fabricated on Highly Orientated Pyrolytic Graphite (HOPG) by Electrodeposition", *Electrochimica Acta*, Volume 114, pp. 379-386, 2013.
- [9] Bai, Y., Yang, T., Gu, Q., Cheng, G., and Zheng, R., "Shape Control Mechanism of Cuprous Oxide Nanoparticles in Aqueous Colloidal Solutions", *Powder Technology*, Volume 227, pp. 35-42, 2012.
- [10] Majumder, M., Biswas, I., Pujaru, S., and Chakraborty, A., "Cuprous Oxide Thin Films Grown by Hydrothermal Electrochemical Deposition Technique", *Thin Solid Films*, Volume 589, pp. 741-749, 2015.
- [11] Chang, Y., Teo, J.J., and Zeng, H.C., "Formation of Colloidal CuO Nanocrystallites and Their Spherical Aggregation and Reductive Transformation to Hollow Cu<sub>2</sub>O Nanospheres", *Langmuir*, Volume 21, No. 3, pp. 1074-1079, 2005.
- [12] Rakhshani, A.E., "Preparation, Characteristics and Photovoltaic Properties of Cuprous Oxide - A Review", *Solid-State Electronics*, Volume 29, No. 1, pp. 7-17, 1986.
- [13] Robotjazi, H., Zhao, H., Swearer, D.F., Hogan, N.J., Zhou, L., Alabastri, A., McClain, M.J., Nordlander, P., and Halas, N.J., "Plasmon-Induced Selective Carbon Dioxide Conversion on Earth-Abundant Aluminum-Cuprous Oxide Antenna-Reactor Nanoparticles", *Nature Communications*, Volume 8, No. 1, pp. 27, 2017.
- [14] Lu, Y., Wang, T., Tian, Z., and Ye, Q., "One-Pot Synthesis of Cuprous Oxide-Reduced Graphene Oxide Nanocomposite as an Anode Material for Lithium Ion Battery", *International Journal of Electrochem Science*, Volume 12, pp. 3941-3949, 2017.
- [15] Hou, Y., Hu, W., Gui, Z., and Hu, Y., "Effect of Cuprous Oxide with Different Sizes on Thermal and Combustion Behaviors of Unsaturated Polyester Resin", *Journal of Hazardous Materials*, Volume 334, pp. 39-48, 2017.
- [16] Wang, H., Zhang, Y., Wang, Y., Ma, H., Du, B., and Wei, Q., "Facile Synthesis of Cuprous Oxide Nanowires Decorated Graphene Oxide Nanosheets Nanocomposites and Its Application in Label-Free Electrochemical Immunosensor", *Biosensors and Bioelectronics*, Volume 87, pp. 745-751, 2017.
- [17] Rezaie, A.B., Montazer, M., and Rad, M.M., "Antibacterial, UV Protective and Ammonia Sensing Functionalized Polyester Fabric Through in Situ Synthesis of Cuprous Oxide Nanoparticles", *Fibers and Polymers*, Volume 18, No. 7, pp. 1269-1279, 2017.