



## Synthesis and Characterisation of CdS Sensitized TiO<sub>2</sub> Solar Cell

S. Shri Prasad\*, D. Arun kumar, J. Madhavan

Department of Physics, Loyola college, Chennai, TN, India.

Received : 16.07.2013 Accepted:19.12.2013

### Abstract

Titanium dioxide TiO<sub>2</sub> nano particles of size around 13nm were synthesized by sol-gel method using titanium (IV) isopropoxide, isopropyl alcohol and NH<sub>3</sub> precursors. The XRD diffraction pattern shows the anatase structure of TiO<sub>2</sub> and FESEM shows the particle size of TiO<sub>2</sub> is 13 nm. Nanostructured TiO<sub>2</sub> thin films were prepared by doctor blade method on an indium tin oxide (ITO) coated glass substrate. The mesoporous TiO<sub>2</sub> thin film was sensitized by cadmium sulfide (CdS) by successive ionic layer absorption and reaction (SILAR) method. CdS sensitized solar cell was fabricated by following standard dye sensitized solar cell fabrication method. It was tested under standard illumination 1.5 AM, 100mW cm<sup>-2</sup>. The photo energy conversion efficiency of the CdS sensitized solar cell was observed as 1.31%.

**Keywords:** Titanium dioxide; Sol-gel; Doctor-blade; Solar cell; Cadmium sulfide.

### 1. INTRODUCTION

Integration of nanostructured materials in the photo voltaic cells can open up the possibilities of developing low cost solar cells (Arun Kumar *et al.* 2013). TiO<sub>2</sub> in the anatase form appears to be the most photoactive and stable material under UV radiation. By doping or sensitization, it is possible to improve the photoactivity of TiO<sub>2</sub> nanomaterials in the visible region (Holfmann *et al.* 2010). Dye sensitized solar cells (DSSCs) were widely studied in the prospects of low cost investment and fabrication compared with other solar cell technologies (Hagfeldt *et al.* 2010). Recently DSSC reached the solar conversion efficiency of 12.3% (Yella *et al.* 2011). Currently, inorganic photo sensitized solar cells are being considered instead of organic dyes for their thermal stability (Jang *et al.* 2012).

### 2. EXPERIMENTAL

#### 2.1 Synthesis of TiO<sub>2</sub> powder

The solution of titanium (IV) isopropoxide Ti(OC<sub>3</sub>H<sub>7</sub>)<sub>4</sub> (Aldrich) was added dropwise in the isopropyl alcohol (Merck) and stirred for 30 min. The metal oxide gel was produced by increasing the pH by dropwise addition of 1 N NH<sub>3</sub> (Merck) solution. The resultant solution was stirred for 24 h and kept 1 day for aging. The precipitate was washed several times with distilled water and ethanol and dried in oven at 100 °C for 3 h to remove the solvent. It was calcinated at 400 °C for 3 h.

#### 2.2 Preparation of Photoanode

A paste of TiO<sub>2</sub> nanopowder was prepared by the addition of few drops of poly vinyl alcohol. It was coated on ITO (15 Ω sq<sup>-1</sup>, Sigma) substrate by doctor blade method to get approximately 10mm thick film and dried at 450 °C for 2 h (Wang *et al.* 2003).

---

\* S. Shri Prasad

E-mail: geoshri@gmail.com

This thin film was dipped 6 times in the aqueous cadmium chloride  $\text{CdCl}_2$  (Merck) and sodium sulfide  $\text{Na}_2\text{S}$  (Merck) solutions alternatively which leads to the formation of cadmium sulfide  $\text{CdS}$  inside the porous structure of  $\text{TiO}_2$  thin film and becomes photo sensitive film.

### 2.3 Fabrication of the solar cell

The photosensitive electrode and the carbon coated ITO counter electrode were separated by a spacer ( $\sim 50 \mu\text{m}$  thick) and sealed by a standard Epoxy Adhesive (Araldite, Hindustan). The iodine electrolyte was inserted between the electrodes by capillary action and sealed.

## 3. RESULT & DISCUSSION

The prepared  $\text{TiO}_2$  powders were characterized by X-ray diffractometer (RAYOS-X) with monochromatic  $\text{CuK}(\lambda=1.5418 \text{ \AA})$  radiation and the planes (101), (004), (200), (105), (211), (204) corresponding to the angles  $2\theta$  in the Fig.1 indicates the anatase structure of  $\text{TiO}_2$  (JCPDS 73-1764). The FESEM image was taken by F E I Quanta FEG 200 in the Fig.2 shows the prepared thin film contains  $\text{TiO}_2$  nano spheres of size 13 nm on the ITO glass plate.

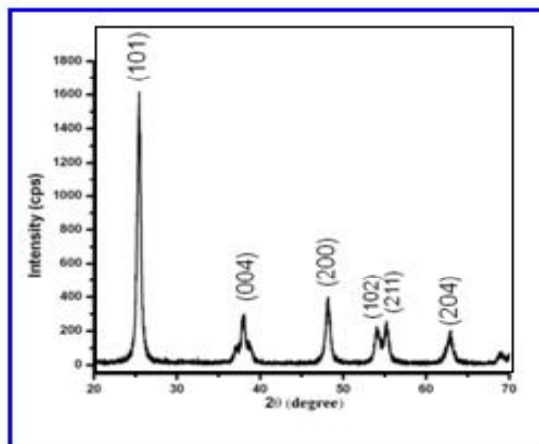


Fig.1: X-ray diffraction pattern of  $\text{TiO}_2$

The UV-Vis spectrum in the Fig.3 shows the first absorption maximum at the wavelength 355 nm. The Tauc plot in the Fig.4 shows that the band gap energy of the synthesized  $\text{TiO}_2$  powder is 3.2 eV.

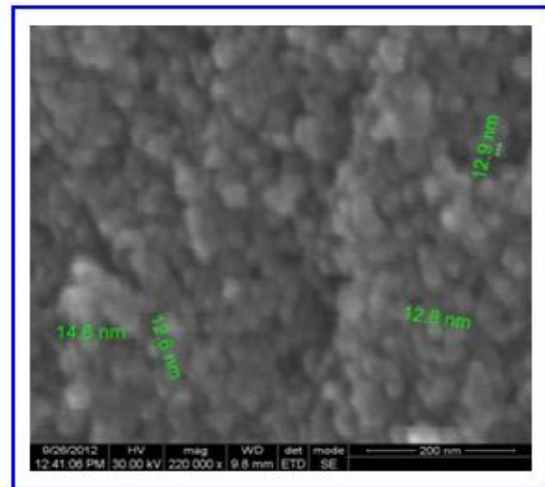


Fig. 2: FESEM image of  $\text{TiO}_2$  thin film

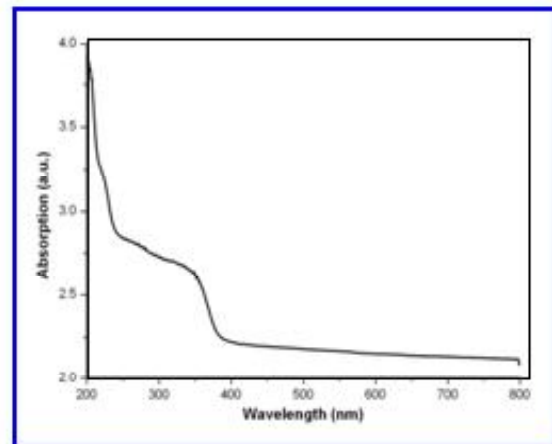


Fig. 3: Absorption spectrum of  $\text{TiO}_2$

The I-V characteristics of the photovoltaic cell was observed by applying an external bias to the cell and measuring the generated photo current with a source meter (Keithley 2400) under the illumination of  $100 \text{ m W cm}^{-2}$  using 450 W xenon

lamp (New port 91160 A) which is equivalent to 1.5 A.M of solar spectrum of  $1000 \text{ Wm}^{-2}$ .

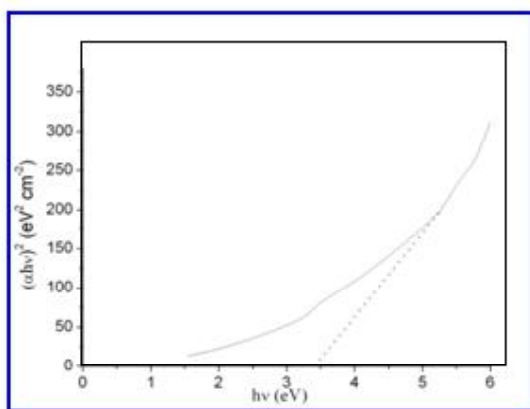


Fig. 4: Tauc plot for  $\text{TiO}_2$

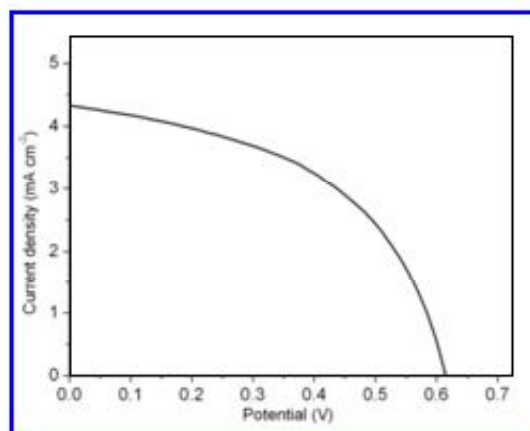


Fig. 5: I-V Characteristics of solar cell

The I-V characteristics of the solar cells with the CdS sensitizer were shown in the Fig.5 and the corresponding, short circuit photocurrent density ( $J_{sc}=4.329 \text{ mA}$ ), open voltage ( $V_{oc}=0.615 \text{ V}$ ), fill factor ( $FF=49$ ) and efficiency ( $\eta=1.31\%$ ) The photo conversion efficiency of the solar cell with CdS sensitizer was due to the photoactivity of the CdS for visible radiation.

Photo excited electrons generated by the CdS sensitizers are injected into the wide band gap semiconductor  $\text{TiO}_2$  and reached the ITO, while holes are transferred to the counter electrode via a redox electrolyte. The voltage generated under illumination corresponds to the difference between electrochemical potential of the electron at the two contacts, which is the difference between the Fermi level of the CdS sensitized  $\text{TiO}_2$  layer and the redox potential of the electrolyte. Over all, electric power is generated without permanent chemical transformation.

#### 4. CONCLUSION

The anatase form of nano structured  $\text{TiO}_2$  thin films were deposited on ITO substrates by doctor blade method. From the XRD and FESEM image the size and structure of the thin film were discussed. CdS sensitized solar cell fabrication technique and working principle were discussed. The solar conversion efficiency and fill factor were calculated from the I-V curve drawn from the data obtained under the standard illumination.

#### ACKNOWLEDGEMENT

The Authors thank to DST and SAIF, IIT, Chennai for characterization techniques.

#### REFERENCES

- Arun Kumar, D., Alex Xavier, J., Shyla, J. M., Xavier, F. P., Synthesis and structural, optical and electrical properties of  $\text{TiO}_2/\text{SiO}_2$  nanocomposites, *J. Mater. Sci.*, 48, 3700-3707(2013). <http://dx.doi.org/10.1007/s10853-013-7167-2>
- Hagfeldt, A., Boschico, G., Sun, L., Kloo, L., Pettersson, H., Dye-sensitized solar cells, *Chem. Rev.*, 110, 6595-6663(2010). <http://dx.doi.org/10.1021/cr900356p>.
- Holfmann, M. R., Martin, S. T., Choi W., Bahnemann, D. W., Environmental Applications of Semiconductor Photocatalysis, *Chem. Rev.*, 95, 69-96(1995). <http://dx.doi.org/10.1021/cr00033a004>.

- Jang, W., Nursanto, E. B., Kim, J., Park, S. J., Min, B. K., Yoo, K. P., Liquid carbon dioxide coating of CdS quantum-dots on mesoporous TiO<sub>2</sub> film for sensitized solar cell applications, *J. Supercritical Fluids.*, 70, 40-47(2012). <http://dx.doi.org/10.1016/j.supflu.2012.06.009>.
- Wang, P., Zakeeruddin, S. M., Moser, J. E., Gratzel, M., A New Ionic Liquid Electrolyte Enhances the Conversion Efficiency of Dye-Sensitized Solar Cells, *J. Phys. Chem, B.*, 107, 13280-13285(2003). <http://dx.doi.org/10.1021/jp0355399>.
- Yella, A., Lee, H. W., Tsao, H. N., Yi, C., Chandiran, A. K., Nazeeruddin, Md. K., Diau, E. W. G., Yeh, Y., Zakeeruddin S. M., Gratzel, M., Porphyrin-Sensitized Solar Cells with Cobalt (II/III)-Based Redox Electrolyte Exceed 12 Percent Efficiency, *Science.*, 334, 629-634(2011). <http://dx.doi.org/10.1126/science.1209688>.