



# Application of modified bentonite using sulfuric acid for the removal of hexavalent chromium from aqueous solutions

Masoud Moradi<sup>1</sup>, Aliakbar Dehpahlavan<sup>2</sup>, Roshanak Rezaei Kalantary<sup>3\*</sup>, Ahmad Ameri<sup>3</sup>, Mahdi Farzadkia<sup>3</sup>, Hasan Izanloo<sup>4</sup>

<sup>1</sup>PhD Student of Environmental Health Engineering, School of Public Health, Iran University of Medical Sciences, Tehran, Iran

<sup>2</sup>MSc in Environmental Health Engineering, School of Public Health, Iran University of Medical Sciences, Tehran, Iran

<sup>3</sup>Professor, Department of Environmental Health Engineering, School of Public Health, Iran University of Medical Sciences, Tehran, Iran

<sup>4</sup>Associate Professor, Department of Environmental Health Engineering, School of Public Health, Qom University of Medical Sciences, Qom, Iran

## Abstract

**Background:** Environmental contamination by chromium (Cr) has become an important issue due to its adverse effects on human health and environment. This study was done to evaluate the application of modified bentonite using sulfuric acid as an adsorbent in the removal of hexavalent Cr from aqueous solution.

**Methods:** Adsorbent features were determined using x-ray diffraction (XRD), fourier transformed infrared spectroscopy (FTIR) and scanning electron microscope (SEM) techniques. Thereafter, the effect of pH, contact time, adsorbent dosage and different concentrations of Cr was investigated. The experimental data was fitness in terms of kinetic and equilibrium adsorption processes.

**Results:** The maximum capacity (Q<sub>m</sub>) of Cr(VI) according to Langmuir model was obtained at 4.21 mg/g. The experimental data properly obeyed the Langmuir and pseudo-second-order models. The highest percentage of Cr(VI) adsorption was observed at pH=3 and the process after 60 minutes reached the equilibrium state.

**Conclusion:** In Langmuir expression, the dimensionless constant separation term (RL) values for the adsorption of Cr onto the modified bentonite was in the range of 0-1, indicating that the adsorption is a favorable process and the modified bentonite has good potential in removing hexavalent Cr using sulfuric acid.

**Keywords:** Modified bentonite, Sulfuric acid, Adsorption, Hexavalent chromium, Aqueous solution

**Citation:** Moradi M, Dehpahlavan A, Rezaei Kalantary R, Ameri A, Farzadkia M, Izanloo H. Application of modified bentonite using sulfuric acid for the removal of hexavalent chromium from aqueous solutions. *Environmental Health Engineering and Management Journal* 2015; 2(3): 99–106.

## Article History:

Received: 7 June 2015

Accepted: 2 August 2015

ePublished: 12 September 2015

## \*Correspondence to:

Roshanak Rezaei Kalantary

Email: rezaei.r@iums.ac.ir

## Introduction

Environmental contamination by chromium (Cr) has become an important issue due to the potential hazard it poses to living organisms (1). The oxidation state of Cr includes 2 forms: Cr(VI) and Cr(III); of which Cr(VI) form is toxic to environment, due to its carcinogenicity, toxicity and high aqueous solubility (2,3). The maximum allowable discharge of Cr in aquatic environments is 0.05 mg/dm<sup>3</sup>, whereas the total Cr should be less than 2.0 mg/dm<sup>3</sup> (4). Cr(VI) in concentrations more than 50 has irreversible effects on kidney and liver, and can cause skin and lung cancer, as well as allergic problems (5). For these reasons, researchers have used several methods, such as ion exchange, ultrafiltration, reverse osmosis, electro dialysis, chemical precipitation, evaporation, solvent extraction, membrane processes coagulation, flocculation, biological treatment and chemical oxidation to remove or reduce Cr (6).

The use of these methods are limited because of high cost, the need for chemical matters, waste disposal, low efficiency, high demand for energy, etc. (7-9). While, adsorption method is widely used to remove heavy metals, due to its simple design and easy operation, proper efficiency and low cost (10). In previous studies, different adsorbents have been used to remove Cr, including both organic and inorganic materials, such as granular activated carbon (GAC), powder activated carbon (PAC), mineral cartridge, biological and agricultural waste, hydrochloric acid (HCL), modified bentonite and natural bentonite (11-16). Despite the higher maximum adsorption capacity of PAC (49.6 mg/g), this adsorbent has some problems, such as its reusability and higher production costs (17). Thus, using adsorbents that have high efficiency in removing contaminants, in addition to having some benefits, such as inexpensiveness, availability, reusability and easy modification, can play important role in this field.



The study of Slimane et al (18) showed that the bentonite has cost-effective recovery, and reusability without appreciable loss of performance. One way to establish the increase of mineral adsorbents, such as bentonite treated by acids, is using sulfuric acid. Results of Salem and Karimi (19) and Alemdaroglu et al (20) indicated that the treatment of bentonite using sulfuric acid changed its chemical properties, increased its specific surface area and surface acidity of the adsorbent. Since sulfuric acid is more effective than more acids such as HCL acid due to changes in the chemical properties of the adsorbent (21) and changes in the physicochemical properties of bentonite, such as crystallinity of its smectite, chemical composition, cation exchange capacity, adsorption capacity and selectivity, porosity, surface area, surface acidity, and catalytic power by acid modification (22), this study was undertaken to evaluate the application of modified bentonite using sulfuric acid in the removal of hexavalent Cr in aqueous solution.

## Methods

### Adsorbent preparation

At the beginning, bentonite granules, obtained from Zanjan region of Iran, were washed with distilled water, dried in an oven at 103°C for 6 hours and crushed and sieved through a 50 mesh sieve. Then, the adsorbent modification was conducted by adding 50 g of the bentonite to 500 mL of sulfuric acid solution (3M) and refluxing at 110°C under atmospheric pressure in a round bottomed flask equipped with a reflux condenser for 4 hours. The resulting bentonite suspension was then rapidly quenched by adding 500 mL ice cold water. The content was filtered, repeatedly washed with distilled water to remove any unspent acid and dried in an oven, calcined at 500°C for 1 hour (23). Finally, the prepared adsorbent was stored in an air tight container for future use.

### Adsorbate

A stock solution of Cr(VI) (1000 mg/L) was prepared by dissolving certain amount of potassium dichromate ( $K_2Cr_2O_7$ ) in deionized water and the considered concentrations (20-100 mg/L) were prepared by diluting the stock solution. The residual concentration of Cr(VI) was measured using a UV-VIS spectrophotometer (7400CE CECIL) at 540 nm by diphenylcarbazide method (17).

### Characterization of the modified bentonite

The X-ray diffraction (XRD) (model Shimadzu XRD – 6000), fourier transformed infrared spectroscopy (FTIR) (model WQF-510), differential thermal analysis (DTA) and scanning electron microscope (SEM) (model Philips XL30) analysis were used for the characterization of acid treated bentonite. XRD was employed to determine the diffraction pattern of the natural and modified bentonite. SEM technique was used to analyze the surface morphology of the natural and modified bentonite. The functional groups of the modified bentonite were also determined using FTIR.

### Batch adsorption experiments

To establish the experiments in batch condition, 100 mL Erlenmeyer flasks containing 20 mg/L Cr(VI) and a certain amounts of the adsorbent were used. All experiments were conducted at a constant rate of 220 rpm at  $20 \pm 2^\circ C$ . pH in the range of 3-10 was selected to determine its effect on adsorption efficiency. Herein, the pH of the solutions was adjusted using 0.1M HCL and/or 0.1M NaOH. Optimal contact time was obtained through 0.5 g/L adsorbent, 20 mg/L Cr(VI) and room temperature at optimum pH. The effects of adsorbent dosage and initial concentration of Cr(VI) were examined in the range of 0.1-2 g/L and 20-100 mg/L, respectively. All experiments were performed in triplicate and average values of the data were reported as the final results. The amount of Cr(VI) adsorbed onto the adsorbent was calculated using the following equation:

$$q_e = \frac{(C_0 - C_e)V}{m}$$

Where  $C_0$  and  $C_e$  are the initial and equilibrium concentration of Cr(VI) (mg/L), respectively. V is the volume of the solution (L) and m is the weight of the modified bentonite (g).

### Adsorption isotherm

Adsorption isotherm describes the equilibrium of the adsorption material at the surface of adsorbent (i.e., at the surface boundary). In this study, Langmuir and Freundlich isotherm models were used to predict the behavior of Cr(VI) adsorption onto the modified bentonite to production.

#### Langmuir Isotherm

The Langmuir equation is based on assumptions, which the maximum adsorption occurred due to a saturated monolayer of adsorbate molecules on the adsorbent surface. Non-linear equation of Langmuir isotherm is as follows (7).

$$q_e = \frac{Q_m b C_e}{1 + b C_e}$$

Where  $q_e$  is the amount of adsorbed material at equilibrium (mg/g),  $C_e$  is the equilibrium concentration (mg/L), b is the affinity parameter or Langmuir constant (L/mg) and  $Q_m$  is the maximum adsorption capacity (mg/g).

#### Freundlich Isotherm

The Freundlich isotherm is based on multilayer adsorption on the heterogeneous surface of the adsorbent containing an unequal amount of energies. It is not limited to a monolayer adsorption, but also it is applied for multilayer adsorption. Non-linear equation of Freundlich isotherm is as follows (7).

$$q_e = K_f C_e^{1/n}$$

where  $K_f$  and n are the Freundlich constants related to the adsorption capacity and intensity, respectively.

### Kinetics of adsorption

Chemical kinetics deals with the experimental conditions influencing the rate of a chemical reaction. Herein, two kinetic models including the pseudo-first-order and pseudo-second-order were used to analyze the experimental data and model the adsorption process (17).

#### Pseudo-first-order kinetic model

Non-linear and linear equations of pseudo-first-order kinetic are as follows (7):

$$\frac{dq_t}{dt} = K_1 (q_e - q_t)$$

$$\log\left(1 - \frac{q_t}{q_e}\right) = -\frac{k_1}{2.302} t$$

Where  $q_t$  is the amount of heavy metal adsorbed on the modified bentonite at a constant time (mg/g) and  $k_1$  is the pseudo-first-order constant rate ( $\text{min}^{-1}$ ).

#### Pseudo-second-order kinetic model

Non-linear and linear equations of pseudo-second-order kinetic are represented as:


$$\frac{dq}{dt} = k(q_e - q)^2$$

$$\frac{t}{q_e} = \frac{1}{k_2 q_e^2} + \frac{1}{q_e} t$$

Where  $q_t$  and  $q_e$  are the concentration of heavy metals in  $t$  and equilibrium times (mg/g) and  $K_2$  is the constant rate of pseudo-second-order kinetic ( $\text{g mg}^{-1} \text{min}^{-1}$ ).


### Results

Features of natural and modified bentonite in terms of morphology, size and surface were analyzed using SEM as shown in Figure 1A and 1B, respectively. One reflection was observed in region  $2^\circ < 2\theta < 70^\circ$  for the XRD pattern of the natural and modified bentonite. This corresponds to the  $5.76^\circ$  ( $2\theta$ ) value from which the interlamellar distance was found to be  $15.33 \text{ \AA}$ . For the XRD pattern of the modified bentonite, the formation of a porous structure was observed by the shoulder appearing in region  $2^\circ < 2\theta < 8^\circ$  (Figure 2). The x-ray pattern of the modified bentonite sample indicated a slight shift in the position of  $d001$  peak from  $15.33$  to  $16.98 \text{ \AA}$ , which was accompanied by a decrease in intensity (Table 1). Figure 3 shows the

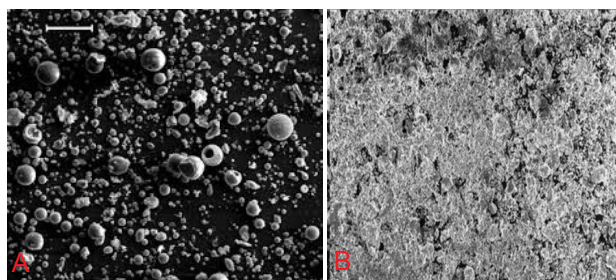


**Figure 1.** SEM microphotographs (Mag. 200X) of A) natural and B) treated bentonite with 3M sulfuric acid.

FTIR spectra of the modified bentonite fraction (KBr pellets with 1% bentonite). Figure 4A shows the effect of pH on Cr(VI) adsorption on the modified and natural bentonite. The maximum Cr(VI) removal occurred at acidic pH (Figure 4A). The effect of contact time on Cr(VI) adsorption was conducted under the following condition:  $0.5 \text{ g/L}$  solution of the adsorbent, optimal pH ( $\text{pH} = 3.0 \pm 0.1$ ) and initial concentration of  $20 \text{ mg/L}$  (Figure 4B). As shown in Figure 4B, Cr(VI) adsorption efficiency was sharply increased up to 45 minutes with increase in contact time, and then gradually reaches the equilibrium state at 60 minutes. Figure 5A and 5B shows the effect of different dosage and initial concentration of the modified and natural bentonite on efficiency removal and adsorption capacity under optimized conditions ( $\text{pH} = 3$  and  $t = 45$  minutes). As illustrated in Figure 5A, with increase in adsorbent dosage (modified bentonite) from  $0.1$  to  $2 \text{ g/L}$ , the removal efficiency of Cr(VI) increased from  $16.85\%$  to  $94.8\%$  for initial concentration of  $20 \text{ mg/L}$ , while the adsorption capacity decreased from  $3.37$  to  $0.95 \text{ mg/g}$ . But with increase in the initial concentration from  $20$  to  $100 \text{ mg/L}$ , the removal efficiency of Cr(VI) decreased from  $73.4\%$  to  $32\%$  for  $0.6 \text{ g/L}$  adsorbent, while the adsorption capacity increased from  $2.44$  to  $5.38 \text{ mg/g}$ . Table 2 shows that the calculated value of constants regarding the Langmuir and Freundlich isotherms for Cr(VI) adsorption on

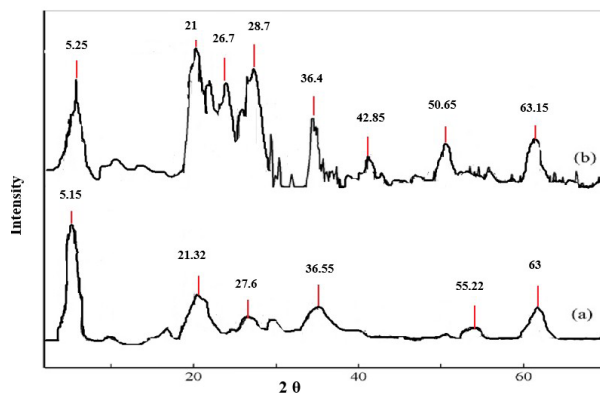



**Figure 2.** XRD patterns of the A) natural bentonite and B) modified bentonite.

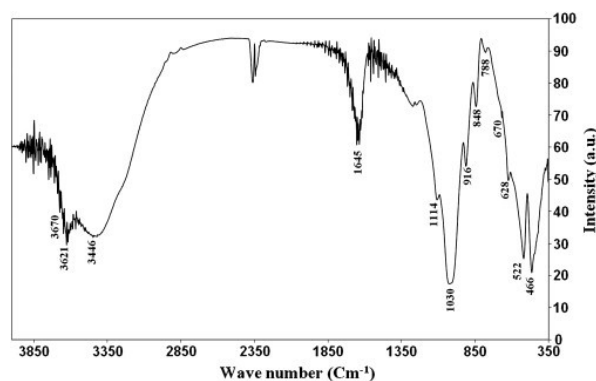

**Figure 3.** FTIR spectra of the modified bentonite fraction (KBr pellets with 1% bentonite).

**Table 1.** XRF analyses (chemical analyses) of natural and modified bentonite

Sample	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	MgO	CaO	Na <sub>2</sub> O	K <sub>2</sub> O
Natural bentonite (%)	55.7	12.85	4.1	3.27	3.48	6.12	0.45
Modified bentonite (%)	65.33	11.74	3.24	2.96	1.87	2.54	0.38

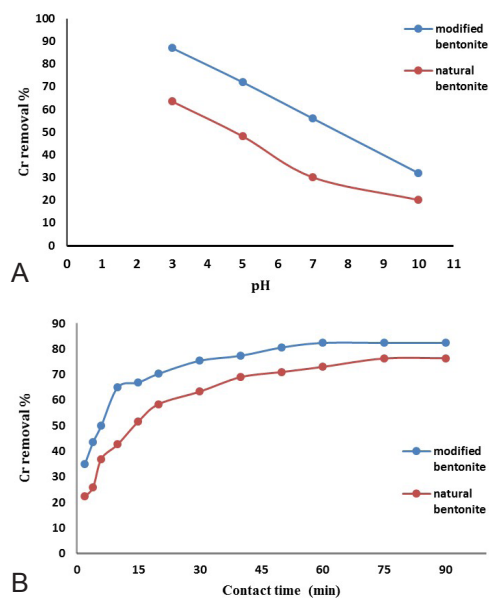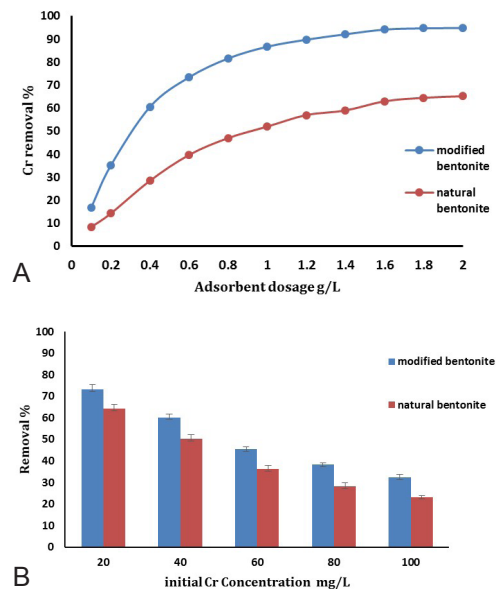**Figure 4.** A) Effect of pH and B) contact time on the adsorption of Cr(VI) on the modified and natural bentonite (200 rpm agitation speed, 0.5 g/L adsorbent, 20 mg/L initial adsorbate, and 25 ± 1°C).**Figure 5.** A) Effect of adsorbate dosage and B) initial Cr(VI) concentration on the removal efficiency of Cr(VI) using the modified and natural bentonite (200 rpm agitation speed, pH = 3, contact time = 45 minutes, and 25 ± 1°C).**Table 2.** Parameters regarding the adsorption isotherm models for Cr(VI) adsorption on modified bentonite

Isotherm model	Parameters	
Langmuir	$q_m$ (mg/g)	4.22
	$K_L$ (L/mg)	0.286
	$R_L$	0.148
	$R^2$	0.992
Freundlich	$K_f$	10.54
	$n$	2.15
	$R^2$	0.974

**Table 3.** Parameters regarding the adsorption kinetic models of Cr(VI) on modified bentonite

Kinetic model	Parameters	
Pseudo first- order	$q_{e,cal}$ (mg/g)	1.297
	$K_1$ (min <sup>-1</sup> )	0.0023
	$R^2$	0.865
Pseudo-second-order	$q_{e,cal}$ (mg/g)	6.53
	$K_2$ (g/mg) (min <sup>-1</sup> )	0.022
	$R^2$	0.996


the modified bentonite at 25 ± 1°C. As shown in Table 2, the adsorption of Cr into the modified bentonite can be described by both Freundlich and Langmuir isotherms. But the correlation coefficient ( $R^2$ ) of isotherms showed that the experimental data best obeyed the Langmuir isotherm model ( $R^2 > 0.99$ ). Table 3 shows the obtained constants values of kinetic models of Cr (VI) adsorption on the modified bentonite with their corresponding regression coefficients. The obtained data indicated that the adsorption kinetics of Cr(VI) onto the modified bentonite is best described by pseudo-second-order model (Figure 6A and 6B). Also, the result showed that there is a significant difference between the modified and natural bentonite efficiency in removing Cr(VI) ( $P < 0.05$ ). Table 4 shows a comparison between the adsorption capacities of various adsorbents for the removal of Cr(VI). The maximum uptake of Cr(VI) per mass unit of modified bentonite was found to be 4.22 mg/g based on the Langmuir model. Moreover, Table 4 shows that the modified bentonite has a proper adsorption capacity compared to many of the adsorbents.

## Discussion

### Adsorbent characteristics

It is clear that the dimension of particles markedly de-



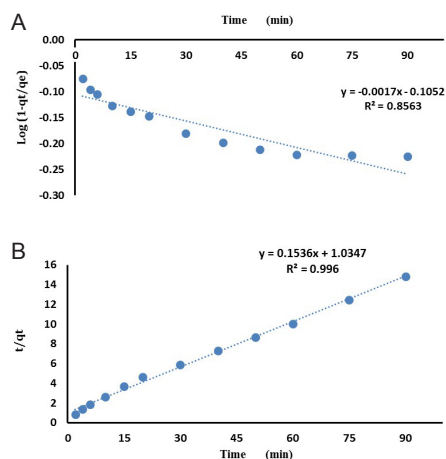

**Figure 6.** A) The pseudo-first-order and B) pseudo-second-order kinetics for adsorption of Cr(VI) on the modified bentonite.

creases due to modification by acid and cation exchange process (19). Additionally, in comparison with the natural bentonite, a porous and heterogeneous surface was observed for the modified bentonite. Hence, it can be concluded that modification of bentonite with sulfuric acid provides an external surface of porous with more reactive sites, which enhanced the adsorption capacity of bentonite. XRD results showed that the exception of  $\text{SiO}_2$  after modification of the adsorbent by acid, other compounds of the adsorbent decreased, and as a result makes it possible to increase the ratio of silica to alumina (24). As result of Panda et al (23) showed that the treatment of kaolin clay by sulfuric acid caused the change of silica to alumina ratio (increased the Si/AL). The XRD pattern of the modified bentonite shows poor crystallinity, broad and less intense peaks as compared to the parent clay mineral due to the presence of layers activated with hydrogen ions, or an irregular stacking of the activated and non-activated layers and thus the structure of the resultant clay becomes amorphous to XRD (25). The FTIR pattern of the modified bentonite shows that some sharp peaks, located between 522 until 1065  $\text{cm}^{-1}$  that indicated Si-O-Al bands (26). These sharp peaks are resulting increase of Si to Al ratio after acidic treatment (27). FTIR spectrum of adsorbent showed that peaks at 3632 and 3426  $\text{cm}^{-1}$  are O-H stretching and H-O-H hydrogen-binding water. The peak of 1643  $\text{cm}^{-1}$  is corresponded to H-O-H deformation (28). Band around 1030  $\text{cm}^{-1}$  is due to Si-O-Si and the peak observed at 783  $\text{cm}^{-1}$  is due to Si-O stretching of quartz and silica. Peaks at 514 and 467  $\text{cm}^{-1}$  can be attributed to Al-O-Si and Si-O-Si deformation, respectively (26).

#### Effect of pH

One of the important parameters which could have more effect on adsorption process is the solution pH (29). The maximum Cr(VI) removal occurred at acidic pH; this is attributed to the electrostatic attraction between the Cr(VI) anions and the adsorbent surface positive charges.  $\text{CrO}_7^{-2}$ ,  $\text{HCrO}_4^-$ ,  $\text{Cr}_3\text{O}_{10}^{-2}$  and  $\text{Cr}_4\text{O}_{13}^{-2}$  ions are the major

**Table 4.** Maximum adsorption capacities ( $q_m$ ) of Cr(VI) on the modified bentonite and other adsorbents documented in the literature

Adsorbent	Qm (mg/g)	Ref.
Single-walled carbon nanoTubes (SWCNTs)	44.64	(6)
Multi-walled carbon nanotubes (MWCNTs)	25.64	
Powdered scoria	2.828	(7)
Commercial iron powder	17.24	(39)
Potato peelings	3.28	(40)
Coffee polyphenol-formaldehyde/ acetaldehyde resins	19.34	(41)
Chemically activated carbon prepared from locally available waste of bamboo	59.23	(42)
Magnetic nanoparticles stabilized by tea-waste	24.9	(43)
Bentonite	4.68	(44)
Xanthan polymer B82	1.68	(45)
Granular ferric hydroxide	0.788	(46)
Hydrous stannic oxide	3.48	(47)
Neem leaf powder	7.43	(48)
Wheat bran	0.94	(49)
This study	4.22	-

species of Cr(VI) at acidic pH conditions, which can be easily adsorbed on the modified bentonite through the electrostatic attraction (3). Similar observation has been reported in the literature (2,17,30). But, decrease in Cr(VI) removal in alkaline conditions, can be due to the negative charges of the bentonite surface in alkali pH that makes electrostatic repulsion between Cr(VI) inions and the adsorbent (26,31). Hence, with increase of pH values, the adsorption efficiency was decreased. This can be explained by the fact that at higher values of pH, Cr is as  $\text{CrO}_4^-$  form that has repulsion state with  $\text{SiO}_2$  which have been formed at high pH. But in lower pH, due to the high hydrated radius,  $\text{HCrO}_4^-$  is absorbed by  $\text{Si}^{+3}$  in the most acidic pH (7). Because the  $\text{pH}_{\text{ZPC}}$  of the modified bentonite was obtained at 4.5, therefore, at pH values less than 4.5, the surface is positively charged and caused electrostatic attraction between  $\text{CrO}_7^{-2}$ ,  $\text{HCrO}_4^-$ ,  $\text{Cr}_3\text{O}_{10}^{-2}$  and  $\text{Cr}_4\text{O}_{13}^{-2}$  ions species of Cr(VI) and the adsorbent surface that resulted caused more removal of Cr(VI) in the solution (17,30). Herein, the maximum Cr(VI) adsorption (87%) was obtained at  $\text{pH}=3$ ; this pH was selected as the optimum. This result is in good agreement with previous studies (32).

#### Effect of contact time

Cr(VI) adsorption efficiency was sharply increased up to 45 minutes and then gradually reaches the equilibrium state at 60 minutes; increase in adsorption efficiency by increasing the contact time can be due to the existence of abundant vacant active sites in the adsorbent surface. However, with increase in contact time, the availability of Cr(VI) ions to the active sites on the adsorbent surface would be limited, which makes the adsorption efficiency to reduce (17). Some studies described similar phenomenon for Cr(VI) adsorption on the different adsorbents (33,34). For example, the result of the study of Moradi et al (7) showed that the adsorption of Cr by scoria reached

the equilibrium state at 60 minutes, while Tang et al (35) showed that the adsorption of Cr(VI) on nano-carbonate hydroxyl apatite reached the equilibrium state at 90 min and at different concentrations of Cr(VI).

#### Effect of adsorbent dosage

The removal efficiency of Cr(VI) increased from 16.85% to 94.8% for the initial concentration of 20 mg/L, while the adsorption capacity decreased from 3.37 to 0.95 mg/g. More availability of active sites on the modified bentonite can cause increase in the adsorption efficiency of Cr(VI) ions (7). Jung et al (8) reported that the removal efficiency of Cr(VI) was raised with increase in the adsorbent dosage. However, a decrease in the adsorption capacity with an increase in the adsorbent dosage is probably due to instauration of the active sites on the adsorbent surface during the adsorption process (17).

#### Effect of different chromium concentrations

With increase in the initial concentration of Cr(VI) from 20 to 100 mg/L, the removal percentage decreased from 86% to 14% (modified bentonite). Few active sites on the surface of the adsorbent seem to be the main reason for the aforementioned result (2,8). Also, the results showed that increase in the initial concentration of Cr(VI) have a positive impact on the adsorption capacity. This phenomenon may be attributed to the rise in the concentration gradient, which is similar to the findings by Cho et al (29) and Luo et al (2).

#### Adsorption isotherm

According to the result, adsorption of Cr into the modified bentonite can be described by both Freundlich and Langmuir isotherms; but the correlation coefficient ( $R^2$ ) of the isotherms showed that the experimental data best obeyed the Langmuir isotherm model ( $R^2 > 0.99$ ). This means that the Langmuir model can be proper to describe the experimental data. Based on this model, it was concluded that the active sites on the modified bentonite surface were distributed in homogeneous form, and monolayer adsorption manner was dominant in the adsorption of Cr(VI) (36). Najafpoor et al (6) reported that the isotherm data of Cr adsorption onto means of carbon nanotubes were obeyed by both Langmuir and Freundlich models, although the Langmuir isotherm was determined to be the most appropriate model.

The  $R_L$  value was between 0 and 1, which suggests that Cr(VI) ions have been desirably adsorbed on the modified bentonite (37). Similar results have also been reported by other researchers on the study of Cr(VI) adsorption on pumice and volcanic rock (5,29). The amount of adsorption intensity ( $1/n$ ) between 0 and 1 indicated that Cr adsorption on the used adsorbent was a favorable process (38).

#### Kinetics of adsorption

The obtained data indicated that the adsorption kinetics

of Cr(VI) onto the modified bentonite is best described by pseudo-second-order model, which is in agreement with previous reports on Cr(VI) adsorption (17,50,51). Moreover, the adsorption capacity ( $q_{e,cal}$ ) calculated from the pseudo-second-order model is best suited for the experimental data ( $q_{e,exp}$ ).

#### Conclusion

Modified bentonite with sulfuric acid was used as an adsorbent to remove Cr(VI) from the aqueous solutions. The results indicated that the modification process has significant effect on the removal efficiency of Cr(VI). Acidic pH = 3 and contact time of 60 minutes were the optimum conditions for the adsorption process. Moreover, results showed that the experimental data are best obeyed by the Langmuir isotherm and pseudo-second-order kinetic models. Because the modified bentonite has appropriate efficiency in the Cr(VI) removal from the aqueous environment, it can be an appropriate alternative for heavy metals treatment from contaminated waters. However, bentonite is less efficient compare other adsorbents, such as activated carbon, but it is a proper alternative for the removal of contaminants in processes that need large quantities of adsorbents, because of its suitable characteristics, such as availability, inexpensive, reusability and proper ability in removing contaminants and by acidic modification of bentonite, its efficiency would be increased more, due to increase in the surface area.

#### Acknowledgements

This article is the result of an MSc Thesis in the field of Environmental Health Engineering, Public Health School, Iran University of Medical Sciences and the authors wish to acknowledge the invaluable cooperation and support from the deputy and chemistry laboratory staff of Iran University of Medical Sciences for facilitating the issue of this project.

#### Ethical issues

Ethical issues (including plagiarism, informed consent, misconduct, data fabrication and/or falsification, double publication and/or submission, redundancy, etc.) have been completely observed by the authors.

#### Competing interests

The authors declared that they have no competing interest.

#### Authors' contributions

All authors contributed equally and participated to the data acquisition, analysis and interpretation. All authors critically reviewed, refined and approved the manuscript.

#### References

1. Vieira RS, Meneghetti E, Baroni P, Guibal E, Victor M, de la Cruz G. Chromium removal on chitosan-based sorbents - An EXAFS/XANES investigation of mechanism. Mater Chem Phys 2014; 146(3): 412-7.

2. Luo C, Tian Z, Yang B, Zhang L, Yan S. Manganese dioxide/iron oxide/acid oxidized multi-walled carbon nanotube magnetic nanocomposite for enhanced hexavalent chromium removal. *Chem Eng J* 2013; 234: 256-65.
3. Lv X, Xu J, Jiang G, Xu X. Removal of chromium (VI) from wastewater by nanoscale zero-valent iron particles supported on multiwalled carbon nanotubes. *Chemosphere* 2011; 85(7): 1204-9.
4. Guerra DJL, Mello I, Freitas LR, Resende R, Silva RA. Equilibrium, thermodynamic, and kinetic of Cr(VI) adsorption using a modified and unmodified bentonite clay. *International Journal of Mining Science and Technology* 2014; 24(4): 525-35.
5. Babaei A, Khataee A, Ahmadpour E, Sheydaei M, Kakavandi B, Alaei Z. Optimization of cationic dye adsorption on activated spent tea: equilibrium, kinetics, thermodynamic and artificial neural network modeling. *Korean J Chem Eng* 2015. doi: 10.1007/s11814-014-0334-6.
6. Najafpoor AA, Soleimani G, Ehrampoush MH, Ghaneian MT, RahmanpourSalmani E, Dolatabadi Takabi M. Study on the adsorption isotherms of chromium (VI) by means of carbon nano tubes from aqueous solutions. *Environ Health Eng Manag J* 2014; 1(1): 1-5.
7. Moradi M, Hemati L, Pirsaeheb M, Sharafi K. Removal of hexavalent chromium from aqueous solution by powdered scoria-equilibrium isotherms and kinetic studies. *World Appl Sci J* 2015; 33(3): 393-400.
8. Jung C, Heo J, Han J, Her N, Lee SJ, Oh J, et al. Hexavalent chromium removal by various adsorbents: powdered activated carbon, chitosan, and single/multi-walled carbon nanotubes. *Sep Purif Technol* 2013; 106: 63-71.
9. Vaiopoulou E, Gikas P. Effects of chromium on activated sludge and on the performance of wastewater treatment plants: a review. *Water Res* 2012; 46(3): 549-570.
10. Lv X, Xu J, Jiang G, Tang J, Xu X. Highly active nanoscale zero-valent iron(nZVI)-Fe<sub>3</sub>O<sub>4</sub> nanocomposites for the removal of chromium (VI) from aqueous solutions. *J Colloid Interface Sci* 2012; 369(1): 460-9.
11. Ahn CK, Park D, Woo SH, Park JM. Removal of cationic heavy metal from aqueous solution by activated carbon impregnated with anionic surfactants. *J Hazard Mater* 2009; 164(2-3): 1130-6.
12. Narayanan NV, Ganesan M. Use of adsorption using granular activated carbon (GAC) for the enhancement of removal of chromium from synthetic wastewater by electrocoagulation. *J Hazard Mater* 2009; 161(1): 575-80.
13. Albadarin AB, Mangwandi C, Al-Muhtaseb AH, Walker GM, Allen SJ, Ahmad MN. Kinetic and thermodynamics of chromium ions adsorption onto low-cost dolomite adsorbent. *Chem Eng J* 2012; 179: 193-202.
14. Aliabadi M, Khazaei I, Fakhraee H, Mousavian M. Hexavalent chromium removal from aqueous solutions by using low-cost biological wastes: equilibrium and kinetic studies. *Int J Environ Sci Technol* 2012; 9(2): 319-26.
15. Van Son T, Van Quy T. Research on chromium removal in water by modified bentonite. *VNU J Sci Earth Sci* 2012; 28(1): 37-43.
16. Chakir A, Bessiere J, Kacemi KE, Marouf B. A comparative study of the removal of trivalent chromium from aqueous solutions by bentonite and expanded perlite. *J Hazard Mater* 2002; 95(1-2): 29-46.
17. Kakavandi B, Kalantary R, Farzadkia M, Mahvi AH, Esrafil A, Azari A, et al. Enhanced chromium (VI) removal using activated carbon modified by zero valent iron and silver bimetallic nanoparticles. *J Environ Health Sci Eng* 2014; 12: 115.
18. Slimane RK, Djafri A, Djafri F. The use of bentonite in heterogeneous medium as an efficient recyclable catalyst in the synthesis of iminoesters. *Medit J Chem* 2011; 1(1): 1-7.
19. Salem A, Karimi L. Physico-chemical variation in bentonite by sulfuric acid activation. *Korean J Chem Eng* 2009; 26(4): 980-4.
20. Alemdaroglu T, Akkus G, Onal M, Sarikaya Y. Investigation of the surface acidity of a bentonite modified by acid activation and thermal treatment. *Turk J Chem* 2003; 27: 675 - 681.
21. Huang CC, Li HS, Chen CH. Effect of surface acidic oxides of activated carbon on adsorption of ammonia. *J Hazard Mater* 2008; 159(2-3): 523-7.
22. Onal M, Sarikaya Y. Preparation and characterization of acid-activated bentonite powders. *Powder Technol* 2007; 172(1): 14-8.
23. Panda AK, Mishra BG, Mishra DK, Singh RK. Effect of sulphuric acid treatment on the physico-chemical characteristics of kaolin clay. *Colloids Surf A Physicochem Eng Asp* 2010; 363(1-3): 98-104.
24. Flessner U, Jones DJ, Rozière J, Zajac J. A study of the surface acidity of acid-treated montmorillonite clay catalysts. *J Mol Catal A Chem* 2001; 168(1-2): 247-56.
25. Eren E, Afsin B. An investigation of Cu (II) adsorption by raw and acid-activated bentonite: A combined potentiometric, thermodynamic, XRD, IR, DTA study. *J Hazard Mater* 2008; 151(2-3): 682-91.
26. Foletto EL, Volzone C, Porto LM. Performance of an Argentinian acid-activated bentonite in the bleaching of soybean oil. *Brazilian Journal of Chemical Engineering* 2003; 20(2): 139-145.
27. Jakobsson S. Determination of Si/Al ratios in semicrystalline aluminosilicates by FT-IR spectroscopy. *Appl Spectrosc* 2002; 56(6): 797-799
28. Parthasarathy G, Kunwar AC, Srinivasan R. Occurrence of moganite-rich chalcedony in deccan flood basalts, Killari, Maharashtra, India. *Eur J*

- Mineral 2001; 13(1): 127-34.
29. Cho HH, Wepasnick K, Smith BA, Bangash FK, Fairbrother DH, Ball WP. Sorption of aqueous Zn (II) and Cd (II) by multiwall carbon nanotubes: the relative roles of oxygen-containing functional groups and graphenic carbon. *Langmuir* 2010; 26(2): 967-81.
  30. Yuan P, Liu D, Fan M, Yang D, Zhu R, Ge F, et al. Removal of hexavalent chromium (Cr(VI)) from aqueous solutions by the diatomite-supported/unsupported magnetite nanoparticles. *J Hazard Mater* 2010; 173(1-3): 614-621.
  31. Catalfamoia P, Arrigoa I, Primeranoa P, Corigliano F. Zeolitized pumice waste as a low-cost heavy metals adsorbent. *J Hazard Mater* 2006; 134(1-3): 140-143.
  32. Alemayehua E, Thiele-Bruhn S, Lennartz B. Adsorption behaviour of Cr(VI) onto macro and micro-vesicular volcanic rocks from water. *Sep Purif Technol J* 2011; 78(1): 55-61.
  33. Devi BV, Jahagirdar A, Ahmed MZ. Adsorption of chromium on activated carbon prepared from coconut shell. *International Journal of Engineering Research and Applications (IJERA)* 2012; 2(5): 364-70.
  34. Li W, Tang Y, Zeng Y, Tong Z, Liang D, Cui W. Adsorption behavior of Cr(VI) ions on tannin-immobilized activated clay. *Chem Eng J* 2012; 193-194:88-95.
  35. Tang W-Q, Zeng R-Y, Feng Y-L, Li X-M, Zhen W. Removal of Cr(VI) from aqueous solution by nano-carbonate hydroxylapatite of different Ca/P molar ratios. *Chem Eng J* 2013; 223:340-346.
  36. Moracia N, Calabrò PS. Heavy metals removal and hydraulic performance in zero-valent iron/pumice permeable reactive barriers. *J Environ Manage* 2010; 91(11): 2336-2341.
  37. Kakavandi B, Jonidi Jafari A, Rezaei Kalantary R, Nasseri S, Ameri A, Esrafiy A. Synthesis and properties of Fe<sub>3</sub>O<sub>4</sub>-activated carbon magnetic nanoparticles for removal of aniline from aqueous solution: equilibrium, kinetic and thermodynamic studies. *Iran J Environ Health Sci Eng* 2013; 10(1): 1-9.
  38. Kumar PS, Gayathri R. Adsorption of Pb<sup>2+</sup> ions from aqueous solution on to bael tree leave powder: isotherm, kinetics and thermodynamics study. *J Eng Sci Techno* 2009; 4: 381-399.
  39. Rahmani AR, Noorozi R, Samadi MT, Shirzad Siboni M. Removal of hexavalent chromium from aqueous solution by using adsorption onto commercial iron powder; study of equilibrium and kinetics. *Sci J Hamadan Univ Med Sci* 2011; 18(3): 33-9. [In Persian].
  40. Mutongo F, Kuipa O, Kuipa PK. Removal of Cr(VI) from aqueous solutions using powder of potato peelings as a low cost sorbent. *Bioinorg Chem Appl* 2014; 2014: 973153.
  41. Mulani KH, Daniels S, Rajdeo K, Tambe S, Chavan N. Adsorption of chromium (VI) from aqueous solutions by coffee polyphenol-formaldehyde/ acetaldehyde resins. *J Polymers* 2013; 2013: 798368.
  42. Dula T, Siraj K, Kitte SA. Adsorption of hexavalent chromium from aqueous solution using chemically activated carbon prepared from locally available waste of bamboo (*Oxytenanthera abyssinica*). *Environ Chem J* 2014; 2014: 438245.
  43. Babaei AA, Baboli Z, Ahmadi M, Jaafarzadeh N, Goudarzi G. Synthesis tea waste-supported magnetite nanoparticles and study affect onto Removal Chromium Cr(VI) from aqueous solution. *J Ilam Univ Med Sci* 2014; 21(7): 124-33. [In Persian].
  44. Chen YG, He Y, Ye WM, Lin CH, Zhang XF, Ye B. Removal of chromium(III) from aqueous solutions by adsorption on bentonite from Gaomiaozhi, China. *Environ Earth Sci* 2012; 67(5): 1261-8.
  45. Golbabaie F, Ghahri A, Saoudi MR, Rahimi Foroshany A, Tirgar A. Equilibrium and Kinetics of Biosorption of Chromium(VI) from Aqueous Solutions by B82 Xanthan Beads. *Iran J Chem Eng Chem* 2011; 30(2): 11-24. [In Persian].
  46. Asgari AR, Vazi F, Nasseri S, Dordelman O, Mahvi AH, Dehghani Fard E. Removal of hexavalent chromium from drinking water by granular ferric hydroxide. *Iran J Environ Sci Eng* 2008; 5(4): 277-82.
  47. Goswami S, Ghosh UCH. Studies on adsorption behavior of Cr(VI) onto synthetic hydrous stannic oxide. *Water SA* 2005; 31(4): 597-602.
  48. Venkateswarlu P, Venkata Ratnam M, Subba Rao D, Venkateswara Rao M. Removal of chromium from an aqueous solution using *Azadirachta indica* (neem) leaf powder as an adsorbent. *Int J Phys Sci* 2007; 2(8): 188-195.
  49. Nameni M, Moghadam MRA, Arami M. Adsorption of hexavalent chromium from aqueous solutions by wheat bran. *Int J Environ Sci Technol* 2008; 5(2): 161-8.
  50. Momčilović M, Purenović M, Bojić A, Zarubica A, Randelović M. Removal of lead (II) ions from aqueous solutions by adsorption onto pine cone activated carbon. *Desalination* 2011; 276(1-3): 53-9.
  51. Selvarani M, Prema P. Removal of toxic metal hexavalent chromium (Cr(VI)) from aqueous solution using starch-stabilized nanoscale zerovalent iron as adsorbent: equilibrium and kinetics. *Int J Environ Sci* 2012; 2(4): 1962-75.