

REVIEW PAPER

Nano-Fibrous and Tubular Poly (lactic acid) Scaffolds for Vascular Tissue Engineering

Farnaz Sadat Fattahi^{1,*}, Akbar Khoddami¹, Ozan Avinc²

¹ Department of Textile Engineering, Isfahan University of Technology, Isfahan 84156-8311, Iran

² Department of Textile Engineering, Pamukkale University, 20160, Denizli, Turkey

ARTICLE INFO

Article History:

Received 08 June 2019

Accepted 14 August 2019

Published 15 September 2019

Keywords:

In-Vivo, Poly (Lactic Acid)

Scaffold

Vascular-Regeneration

Vessel

ABSTRACT

In recent years, the adaptation of tissue engineering techniques is necessary to progress the field of cardio-vascular bio-logy and advancing patient care. Through the high event of cardio-vascular disease and increasing amount of patients needing vascular admission, there is a considerable require for small-diameter (<6mm inner diameter) vascular graft that can supply long-period patency. Vascular tissue engineering is a novel field that has undergone massive growth more than the final decade and has suggested suitable keys for blood-vessels darn. The objective of vascular tissue engineering is to manufacture neo-vessels and neo-organ tissue from autologous cells by means of a bio-degradable polymer like Poly (lactic acid) (PLA) as a scaffold. PLA Nano-fibrous scaffolds have high surface area-to-volume ratios and porosity that simulate the structure of protein fibers in native extra cellular matrix (ECM). The versatilities of polymer components, fiber structures, and functionalization have made the fabrication of PLA Nano-fibrous scaffolds with suitable mechanical strength, transparency and biological properties for vascular tissue engineering feasible. The most significant benefit of tissue engineered implants is that these tissues can grow, remodel, rebuild, and respond to damage. This review explains the fabrication, properties and advantages of different types of PLA scaffolds with emphasis on Nano-fibrous ones for vascular tissue engineering.

How to cite this article

Sadat Fattahi F, Khoddami A, Avinc O. Nano-Fibrous and Tubular Poly (lactic acid) Scaffolds for Vascular Tissue Engineering. *Nanomed Res J*, 2019; 4(3): 141-156. DOI: 10.22034/nmrj.2019.03.003

INTRODUCTION

Vascular sicknesses have taken the principal choice in death causing diseases generally[1]. Conventional diagrams in managing of vascular illnesses include angioplasty, bypass graft, and auto-graft[2, 3]. Autologous vessels and vascular grafts, to be selected with a small diameter in bypass surgery, are proposed alike as golden option. Vascular tissue engineering has become a hopeful advance in small diameter vessels[4, 5]. Blood-vessels are structurally multifaceted and basically active tissue, with smallest regeneration potential that have composite extracellular matrix (ECM) and arrangement [6, 7]. Natural blood-vessels are categorized into three kinds, which are arteries, veins, and capillaries [8, 9]. Arteries transfer the blood away from the heart and veins

provide the blood back to the heart. Arteriole is the name of small diameter artery[10-12]. The left anterior descending coronary artery offers a main blood supply to the myocardium [13, 14]. Capillaries link arteries and arterioles with vein, and they as well move gases and nutrients to tissues and vice versa[15, 16]. The vessel walls consist of three covers: intima (internal layer), media (central layer), and adventitia (external layer), as exemplified in Fig. 1. Intima layer is a monolayer of endothelial cells[17, 18]. Media layer contains smooth muscle cells (SMCs)[19, 20]. Adventitia layer includes collagenous extracellular matrix (ECM) that holds fibroblast and perivascular nerve cells [4, 21, 22]. Intima, media, and adventitia layers are disconnected from each other by lamina layer having elastin [23-25]. Collagenous

* Corresponding Author Email: fattahi_farnaz@yahoo.com

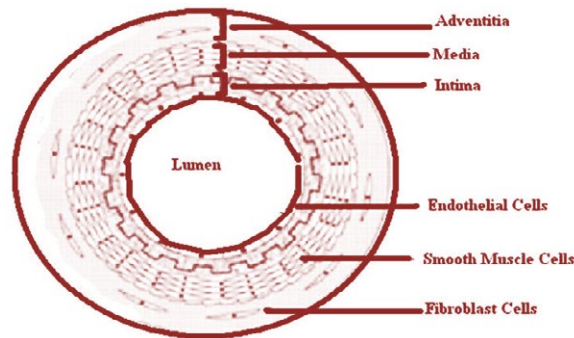


Fig. 1. Scheme of an artery. The arterial wall includes three major layers: (1) adventitia, (2) media and (3) intima. A sheet of endothelial cells coats the inner surface of the lumen whilst smooth muscle cells and fibroblast cells live in external layers[2].

Table 1. ECM components of blood-vessels[37].

Vessel type (diameter)	Elastic artery (30 mm to 5 mm)	Muscular artery (6 mm)	Vein (1–5 mm)	Arteriole (0.50 μm)	Veinule (20–100 μm)	Capillary (0,20 μm)
ECM components	Elastin, fibronectin, fibrillin, fibulin, collagen type I, II, III, IV, V, VI, proteoglycans	Elastin, fibronectin, fibulin, collagen type I, III, IV, V,VI, proteoglycans	Elastin, fibronectin, collagen type I, II, III, IV, VI, XII, XIV proteoglycans	Elastin, collagen I, III, fibrillin	Laminin, collagen IV, fibronectin	Collagen IV, laminin, fibronectin, HSPG

ECM, extracellular matrix; HSPG, heparin sulfate proteoglycan.

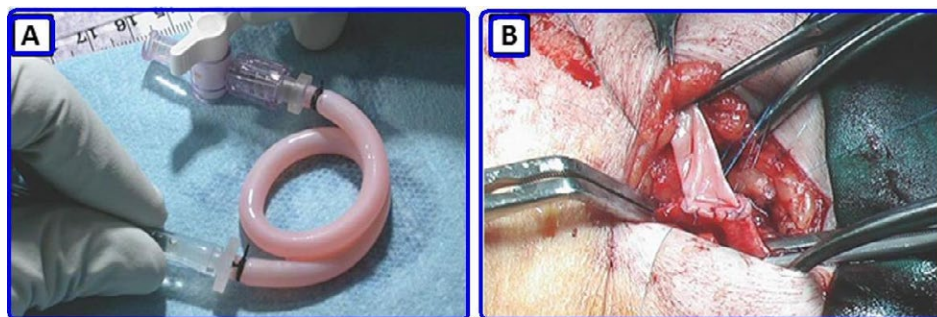


Fig. 2. Tissue engineered blood-vessels: (A) Tissue-engineered graft was implanted among the axillary vein and the humeral artery as an arterio-venous shunt, (B) The vessel exhibited normal suturing and surgical handling properties[13].

adventitia inserts inflexibility to the blood-vessel walls, whereas lamina supplies them with elasticity [4, 26-28]. Endothelial cell (EC) layer is placed at the internal wall of blood-vessel, forbidding the accretion of blood and regulating the quantity of smooth muscle cells (SMCs) in the media layer[29, 30]. Blood-vessels widen and bond in response to a signal from ECs or cytokines [4, 31, 32].

The Extracellular matrix of a blood-vessel varies in its composition (Table 1), thickness, and generally architecture selection from arteries, capillaries to veins [4, 20, 33, 34]. The interaction between ECM pieces and tissue detailed cells

tenders blood-vessels their alert useful character [32, 35, 36].

A perfect scaffold should reproduce the bio-mechanical properties of blood-vessels, as serving like a stage for cell attachment and proliferation [38, 39]. It should be non-thrombogenic, non-immunogenic, bio-compatible and hemo-compatible, bio-degradable with appropriate pore size and elasticity [40-42]. Consequently the scaffold should help the in-vivo regeneration of a tissue engineered vascular mat when implanted at an appropriate location. Vascular tissue engineering tries to development of vascular replacements that

can regenerate in-vivo and act like a native vessel [9, 43, 44]. Widespread study has been carried out on Tissue Engineered Vascular Grafts (TEVGs) over the past few decades [45-47], and as an important development has been made in phrases of attaining the remodeling of the tissue in the TEHV mats similar to the native blood-vessels [48, 49], as depicted in Fig. 2 [13].

Manufacturing the polymeric vascular scaffolds rigorously examined. Different polymers have been employed contain synthetic polymer, natural polymer, and polymer blends [38, 50]. Synthetic polymers display better mechanical properties than natural polymers [51-53]. Blending two synthetic polymers or two natural polymers could consequence in improved mechanical properties. Mechanical properties of artificial blood-vessels play a key function whilst the vessels are attached to the native vessels in the body [9, 50, 51, 54]. If there is a competition in the mechanical properties, the sheer stress, as well as intimal hyperplasia can be evaded [9, 38, 55]. Also, the artificial blood-vessels should be durable sufficient to resist the frequent blood circulation and the related pressure [4, 9, 56, 57]. Fig. 3 displayed some PCL Implanted Scaffolds [2].

POLY (LACTIC ACID)

A variety of efforts have been done to manufacture vascular grafts scaffolds and artificial blood-vessels in tissue engineering by means

of Poly(lactic acid) (PLA) and its co-polymers like Poly(lactide-co- ϵ -caprolactone) (PLCL) and Poly(l-lactide-co-glycolide) (PLGA) [55, 58-62]. The ring open polymerization of lactide, results in PLA which is a chiral molecule that exist in two forms D-PLA and L-PLA [63]. It is bio-degradable thermo-plastic Poly-ester [64-66]. Poly (l-lactide) (PLLA) is a semi-crystalline polymer (~37%) and Poly (dl-lactide) is an amorphous polymer [67, 68], owing to the random distribution of l-lactide and d-lactide units [69-71]. The hydrolytic product of PLLA is lactic acid which is more catabolized in the lactic acid phase into water and carbon Dioxide [72, 73].

This bio-polymer has certain benefits in bio-medical fields like wound dressings, tissue engineering scaffolds, anti-bacterial mats, surgical sutures, drug-delivery systems and gene delivery materials [67, 74-78], that are:

- ✓ PLA can undergo scission in the human body [63, 72, 79, 80].
- ✓ PLA degrades to monomeric units of lactic acid as a natural intermediary in carbohydrate-metabolism [81, 82].
- ✓ PLA has good bio-logical interactions with the host cells when it is implanted [72, 81, 83, 84].
- ✓ The degradation time of PLA have been stated to be around 6 to 12 months [62, 85, 86].

Lactic acid can be polymerized to create PLA polymers by means of direct poly condensation under controlled temperatures and pressures

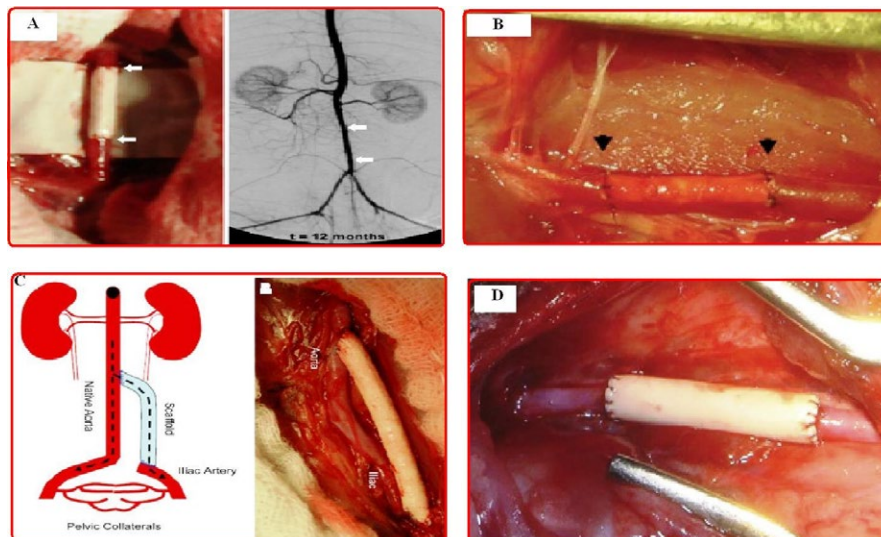


Fig. 3. A) PCL nano-fibrous scaffold implanted in Rat-aorta, B) PCL-CAG peptide nano-fibrous scaffold implanted in Rat-carotid, C) PCL-Collagen nano-fibrous scaffold implanted in Rabbit-aortic-bypass, D) PCL-Elastin nano-fibrous scaffold implanted in Rabbit-carotid [2].

without catalyst, solvent or initiators [87, 88]. The effects of the reaction temperature and pressure on the resulting molecular weights have been studied. The results showed that at 200 °C after about 90 h under vacuum, high molecular weights of 90 kDa can be attained [89, 90]. In addition, other techniques using the organic solvents were developed to formulate poly-DL-lactic acid (PDLLA) via direct solution poly-condensation. In this process the lactic acid, catalysts, and solvents were diversified in a reactor so as to produce high molecular weight polymer of 300 kDa. On the other hand, the greatest usually method to create higher molecular weight PLA was ring-opening polymerization (ROP), occurred by ring opening of the lactide (cyclic dimer of lactic acid) in the presence of a catalyst. This method resulted in production of PLA with a controlled molecular weight [91-93].

This review focuses on the constructing different types of PLA scaffolds like Nano-fibrous scaffolds, Porous scaffolds, Cylinder-shaped scaffolds, Tubular scaffolds and double-porosity scaffolds for vascular regeneration; Cell culturing into the scaffold, non-cytotoxicity of scaffolds and cell adhesion inside them will be reported and the recent advances will be discussed.

APPLICATION OF PLA NANO-FIBERS IN VASCULAR TISSUE REGENERATION

In a novel work in 2018, PLCL were electro-spun for manufacturing nano-fibrous vascular scaffolds, Thrombo-genicity valuation of scaffolds exposed high Thrombo-genic possessions of samples that was comparable to great amount of naturally collagen Thrombo-genicity. The level of platelet activation was dependent on chemical composition and surface-morphology of experienced samples [94].

A different kind of hybrid PLA-Fibrinogen (PLA-FBG) nano-fibrous scaffolds developed in 2017 [14], which have improved stiffness, combining the good mechanical assets of PLA with the excellent cell recognition properties of FBG. HUVECs cells (human umbilical endothelial cells) expanded a stellate-like morphology within multiple shells. The fine-expanded focal adhesion compounds proposed a successful cellular interaction. Nevertheless time-lapse investigation explains notably lowered cell movements, resultant in the cells traversing a quite small space in multiple ways. In opposition, an elongated cell form and considerably increased cell mobility were viewed in aligned nano-fibers.

Time-lapse investigation explained considerably more rapidly wound coverage (within 12 h) of HUVECs on aligned mats vs. approximately absent directional migration on random ones. Though, nitric oxide (NO) release confirms that endothelial cells hold lowered functionality on aligned nano-fibers compared to random samples, wherever considerably higher NO creation was established. Randomly structured nano-fibers could hold the endothelization of implants whereas aligned nano-fibers would slightly direct cell locomotion for guided neovascularization [14].

Tara et al., [95] definite the in-vivo viability of PLA scaffolds coated with PLCL in high pressure, small diameter mouse arterial situations. Large-pore PLA-PLCL grafts prompted a well-organized neointima after 12 months, and Alizarin Red S staining displayed neointimal calcification only in the thin neointima of small-pore PLA nano-fibrous grafts. The vascular smooth muscle cells (VSMCs) of PLLA-PLCL graft expressed transcription factors of both osteoblasts and osteoclasts.

Wang et al. [35] constructed PLLA-Chitosan core-shell nano-composite fibers through a novel method, from heterologous solution through coaxial electro-spinning system was designed for vascular gasket. Chitosan surface was cross-linked by Genipin and modified with heparin. Core-shell structures shaped with a PLA-CS ratio at 1:3. Higher biocompatibility and mechanical properties were achieved by optimizing the core-shell structure morphology and surface cross-linking of CS. UE7T-13 cells grew fine on the core-shell nano-fibers since showing with MTT assays and SEM images. Corresponding to the PLA mats and profitable vascular patch, PLA-CS core-shell nano-fibers had better mechanical strength (Fig. 4). The elastic modulus was 117.18 MPa, although the yield stress of the fibers was lesser than that of the commercial vascular patch. Attachment of red blood cells on the nano-fibers was assessed by blood anticoagulation tests and in vitro blood flow experimentations. SEM images specified there were scarcely any red blood cells attached to the fibers with chitosan coating and heparin modification [35].

In another work, researchers study whether the nano-Hydroxyapatite-PLLA (nHAC-PLLA) scaffold is appropriate to be compounded with VEGF to improve the axial vascularization in vivo. Thirty rabbits were splinted into 2 sets of 15 animals each. In control collection, a PLLA-nHAC scaffold

slice was vascularized axially with an included ligated femoral arterio-venous (AV) bundle in the animal. In experimental set, a piece compounded with VEGF gel was applied. The animals were surrendered at 2 weeks, 6 weeks, and 10 weeks after surgical procedure; the samples of scaffold slices undergo histo-morphometric assessment; examination of the micro-vessel density (MVD) of both groups was done. The blend with VEGF (Group B) did not improve the vascularization in early stage (2 and 6 weeks, $P > 0.05$) but worked in later time (10 weeks, $P < 0.05$) [26].

Deng et al. [62] prepared a cylinder-shaped PLA scaffolds and cultured HUVECs on them. The researchers used Poly Glycolic Acid-PLA (PGA-PLA) mesh for fabrication of scaffolds. Novel air-spun PLA nano-fibers modified with hydrophilic surfaces for vascular tissue engineering is reported by Ko et al.[18]. Surface-initiated atom transfer radical polymerization permits for grafting pendant Oligo (Ethylene Oxide)-holding poly (methacrylate) (POEOMA) from PLA nano-fibers labeled with disulfide linkages (Fig. 5). The resulting PLA-ss-POEOMA fibers exhibit enhanced thermal

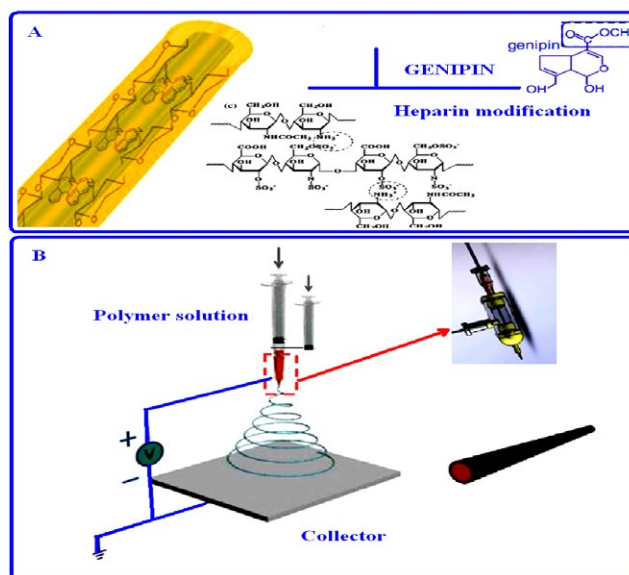


Fig. 4. (A) Illustration of electro-spinning of nano-scaffolds, (B) Illustration of polymer electro-spun[35].

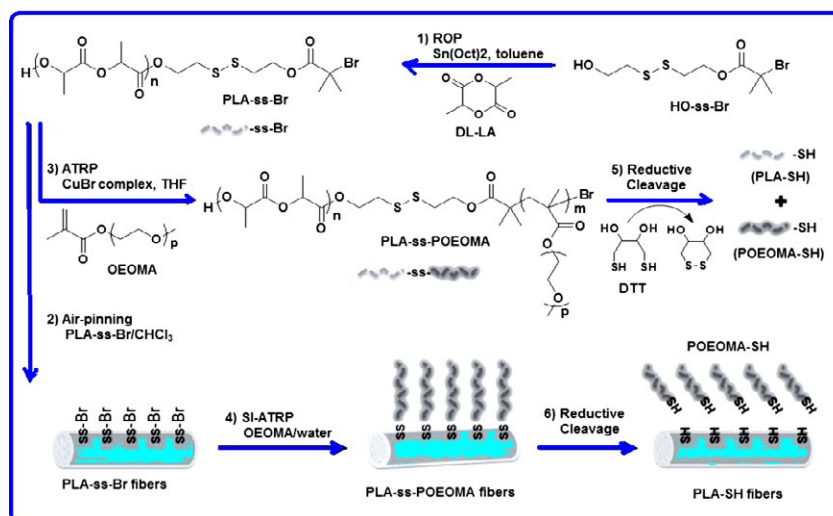


Fig. 5. Illustration of the method to synthesize PLA-ss- POEOMA nano-fibers by surface-initiated atom transfer radical polymerization of OEOMA in the presence of PLA-ss-Br fibrous macro-initiators and their degradation in response to reductive reactions[18].

stability and improved surface properties, as well as Thiol-responsive shedding of hydrophilic POEOMA by the cleavage of its disulfide linkages in response to reductive reactions, thus tuning the surface properties.

In another work, PLLA-Collagen were electro-spun to gain a nano-fibrous scaffold with the best mechanical feature, owing to the presence of PLLA, and capable to signify an optimal substratum for cell adhesion. Bone marrow derived Mesenchymal Stem Cells (MSCs) were seeded on the nano-fibers to explore the ability of these cells for differentiating into vascular endothelial cells while cultivating through differentiating medium. The assays revealed that cells grown on PLLA-Coll nano-fibrous scaffolds differentiated in endothelial cells illustrating cobblestone phenotype with expression of vascular specific proteins, for instance the platelet endothelial cell adhesion molecule-1 [6].

A Different scaffold for vascular tissue engineering was made-up by co electro-spinning PLA-Collagen-Chitosan at room temperature and normal pressure (Fig. 6). By analyzing the effects of composition and collecting distance on the morphology of electro-spun meshes, Zhu et al. [30] stated that the proper collecting distance and the concentration of the solution are the keys to the success of the co-electro-spinning procedure. The outcomes specified that scaffolds fabricated through

co electro-spinning: (a) had a more biomimetic structure than PLA, as the fiber diameters advanced the size of the extracellular matrix; (b) displayed better blood-compatibility. This work proves the feasibility of by means of two different solutions to build a scaffold for blood-vessel tissue engineering via co electro-spinning [30].

Shalumon et al. [96] manufactured aligned and random PLLA-Gel nano-fibers via electro-spinning method. Morphological and chemical characterization of the nano-fibrous scaffolds was carried out and the size of fibers ranged in 100 - 500 nm. The SEM, fluorescent staining and viability examines exposed an increasing in viability and proliferation of Human Umbilical Vein Endothelial Cells (HUVECs) and Smooth Muscle Cells (SMCs) proportional to Gel content. The aligned fiber-morphology comforts cells to orient and elongate along their long axis. Pavia et al. [64] produced PLLA-PLA tubular scaffolds for vascular tissue engineering with different ratios (100-0, 90-10, 75-25 wt-wt) . ECV304 continuous human endothelial cells were cultured on the scaffolds. The outcomes have demonstrated that the scaffold do not make cell toxicity; cells are able to grow into the tubular form scaffold coating its inner surface [64].

Samantha L. Wilson et al. [5] electro-spun multiple orthogonal aligned poly (L, D lactic acid) (PLDLA) scaffolds inoculating human corneal

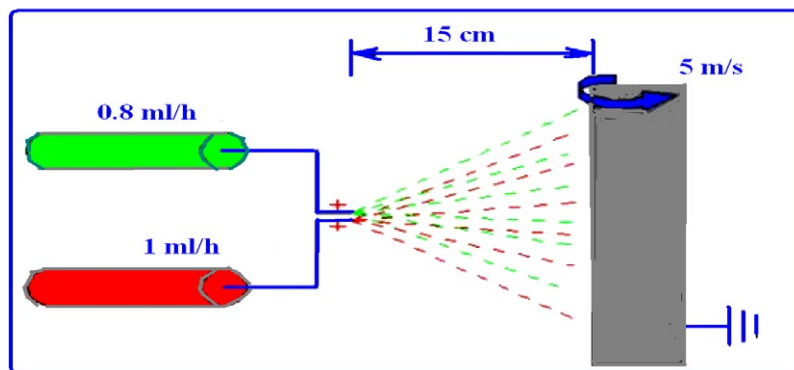


Fig. 6. Scheme of the coelectro-spinning [30].

Table 2. Name and type of PLA scaffolds.

Type of Scaffold	Type of Treatment	Ref.
PLLA	—	[65]
PLLA + COII	Soaked with type—I collagen gel.	[65]
PLLA PdE: N	plasma deposited ethylene : nitrogen coating, PdE:N	
PLLA PdE: N+ COII	Plasma deposited ethylene: nitrogen coating, PdE:N , followed by collagen soaking.	[65]
PLLA PdE:NH2	Plasma deposited ethylene: nitrogen coating, followed by a H2 post treatment.	[65]
PLLA PdE:NH2 + COII	Plasma deposited ethylene: nitrogen coating, followed by a H2 post treatment, followed by collagen soaking.	[65]

stromal cells on the surfaces of them. The matrix elasticity (elastic modulus) and the dimensional changes were analytical of alters in cell phenotype from contractile fibroblasts to quiet keratocytes. Researchers deliberate the persuading of topographical and chemical signals on the phenotypical performances of adult human-derived corneal stromal (AHDCS) cells in 3D (PLDLA) nano-fibrous mats. The results designated that the synergistic effect of nano-fibers and serum-free media plus insulin supplementation offered the most suitable topographical and chemical location for relapsing corneal fibroblasts to a keratocyte phenotype in a 3D construct.

3D PLLA Scaffolds prepared with thermally induced phase separation by Rigogliuso et. al.[65] then treated with plasma processes to modify the surface of them for enhancing cell adhesion on the scaffolds as in Table 2.

Assays proved better interaction of plasma treated scaffolds with HUVEC (Human Umbilical Vein Endothelial Cells) cells compared to untreated ones. Moreover, different chemistry, obtained throughout the two different plasma procedures, permitted different cell behavior. Actually, HUVEC cells seeded on PdE:N scaffolds demonstrated a characteristic Mesenchymal Phenotype of Endothelial Cells, in active proliferation-migration status. In a different way, in scaffolds treated

with PdE:N-H2 plasma method, HUVEC cells illustrated the classical phenotype of cells shaping a differentiated endothelium[65].

PLA-PCL bi-layered tubular nano-fibrous scaffolds fabricated by means of layer-by-layer using electro-spinning method from PCL at the inner layer and PLA at the outer layer. PCL scaffolds consists of microfibers and nano-fibers with diameters of 1.5 μm to 6 μm and 400-600 nm, correspondingly, and interrelated pores with 15 μm average pore size. PLA scaffolds consist of nano-fibers with diameters variety from 800 nm to 3000 nm and interconnected pores with 10 μm average pore-size. The total porosity of PLA-PCL scaffolds is approximately 79 %. The PCL layer imitates the intima sheet of natural blood-vessel, whilst the PLA layer mimics the adventitia cover of natural blood-vessel. The PLA-PCL nano-fibrous scaffolds demonstrate suitable mechanical properties, with Young's modulus of 30.9 MPa nearly three times higher than that of PCL scaffold (10.7 MPa). Fibroblast cells adhered fine to the surface of PLA-PCL scaffolds after four weeks of culturing. Human Venous Myo-fibroblasts (HVS) cells were focused in the outer layer of PCL more willingly than in the inner layer of PLA, which was perhaps owing to the small pore size. On the other hand, the cell content was almost 64% comparable to the native porcine pulmonary valve tissue, signifying the

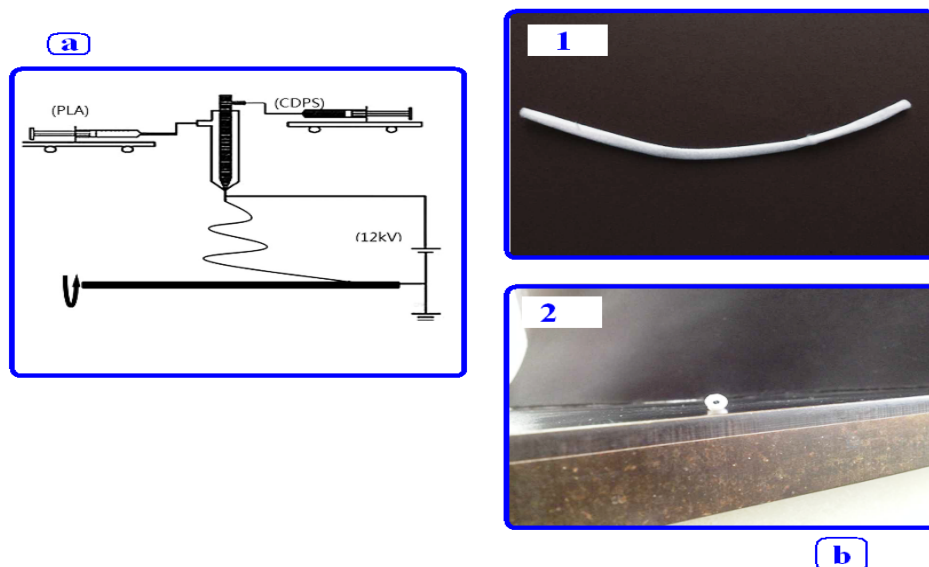


Fig. 7. (a) Co-axial electro-spinning apparatus. The voltage was regulated to constant 12 kV and the distance of coaxial facility to round bar was 10 cm. The flow rate of PLA organic solution and CDPS aqueous solution was 4, 1 (mL/h). A whole scaffold was fabricated with 2 h; (b) 1- Platform of scaffold. The scaffold was 8.7 cm in length and presented white; 2- The cross section of scaffold. The scaffold was hollow and the diameter of cross section was 0.42 cm; (c) 1- Cross-section of the microfiber. The microfiber was produced to form core-sheath structure by means of co-axial electro-spinning technology (500 \times); 2- SEM graph of transplanted scaffold (15 days) [98].

advancement of tissue growth[40].

In another work, Melt electro-spinning technique was employed for the manufacturing of PLA Tubular vascular grafts. It was found that the mass flow rate (MFR) had more important influence on the structure of electro-spun scaffolds when compared to the other fabrication parameters, such as voltage and distance between the spinneret and the collector. Tubular vascular grafts were produced by means of PLA and Poly-Propylene (PP) at the suitable MFR (25 g/10 min and 2.16 kg at 230 °C) [33].

Mixture of cell matrix with electro-spinning technique resulted in constructing PLCL nano-fibrous based vascular grafts seeded with SMCs (Smooth muscle cells). SMCs were cultured for up to 7 weeks[97].

PLA-Silk Fibroin-Gelatin (PLA-SF-Gel) hybrid scaffolds were prepared for vascular tissue engineering and 3T3 mouse fibroblast cells cultured on scaffolds for 21 days that proved good proliferation. In Vivo assays showed that Subcutaneous-implantation investigation in Sprague rat after 3 months caused in bio-compatibility of the graft [24].

Weijie et al.[98] utilized co-axial electro-spinning method for combining Cistanche-Poly (saccharide) [CDPS] with PLA. CDPS and PLA were placed at the internal and outside layer correspondingly so as a core-sheath tubular scaffold was shaped (Fig. 7). Compared to natural tissues, CDPS-PLA co-axial scaffolds presented outstanding bio-mechanic possessions and blood-compatibility, so CDPS-PLA scaffolds retained respectable potential in vascular tissue engineering[98].

Poly (l-lactic acid-co-ε-caprolactone) [P(LLA-CL)] has good mechanical properties but poor biocompatibility. Blending Silk Fibroin (SF) with P(LLA-CL) can preserve the benefits of both these materials and conquer their disadvantages. P(LLA-CL)-SF nano-fibrous membranes may be appropriate for regeneration of the Corneal-Endothelium. Five nano-fibrous scaffolds having different P(LLA-CL)-SF blended ratios (100:0, 75:25, 50:50, 25:75, 0:100) were created. A human corneal endothelial (B4G12) cell line was cultured on the samples. Expression of some useful genes was as well noticed by real-time polymerase chain reaction. The 25:75 blended ratio membranes had the best transmittance among these scaffolds. All electro-spun nano-fibrous membranes demonstrated improved speed of cell adherence when compared with the control collection,

particularly when the P(LLA-CL) ratio increased. The 25:75 blended ratio mats also had the highest cell proliferation. B4G12 cells could appearance a monolayer on all scaffolds, and most functional genes were also steadily expressed on all scaffolds. Just two genes proved changes in expression. All scaffolds confirmed good biocompatibility for cell adherence and monolayer formation. Amongst them, the 25:75 blended ratio P(LLA-CL)-SF nano-fibrous scaffold had the best transmittance and the highest cell proliferation[19].

In a different exploration, Wu et al.[99] fabricated PLCL-Collagen-Chitosan vascular graft in a canine femoral artery by means of electro-spinning process.

Blending of PLLA and Gelatin for enhancing cell adhesion sites were employed in fabricating PLLA-GEL tubular scaffolds for vascular tissue engineering. Aligned and random PLLA-GEL nano-fibers were fabricated via electro-spinning method. The size of fibers ranged from 100 to 500 nm. The SEM, fluorescent staining and viability analyzes tolled an increase in viability and proliferation of Human Umbilical Vein Endothelial Cells (HUVECs) and Smooth Muscle Cells (SMCs) proportional to gelatin substance. The aligned fiber morphology aids cells to orient and elongate along their long axis. Therefore the assays show that topographically aligned nano-fibrous scaffolds manage cellular organization and probably supply a good hold for attaining the vital association and physical properties of blood-vessel [23].

Wang et al.[32] mixed vascular endothelial growth factor (VEGF) with Heparin and overloaded in the core of a Poly(l-lactide-co-caprolactone) nano-fibrous mat using emulsion electro-spinning for helping rapid endothelialization.

In a different research, PLLA-GEL nano-fibrous scaffolds were electro-spun by Zhang et al.[15] and the blended material also exhibited high transparency. Poly (d,l-lactide-co-glycolide)-Collagen (PLGA-Col) blend was used in manufacturing scaffolds (4.75 mm internal diameter, 477 to 765 nm average fiber diameter, and 0.5 mm wall width). The nano-fibrous scaffolds displayed tensile strength of 0.37 MPa and young's modulus of 0.85 MPa, correspondingly[2].

Montini et al.[100] worked on the electro-spinning procedure as an adaptable method for obtaining nano-fibrous tubular constructions for vascular tissue engineering. A bi-layered scaffold composed of Poly(l-lactic acid) and Segmented

Poly(urethane) (PLLA-SPEU) blends for small diameter (5mm) vascular-bypass-grafts was attained with multi-layering electro-spinning[100].

A 50:50 PLCL co-polymer was productively melt-spun and electro-spun to individual and combined

porous tubular scaffolds having dimensions of 5 mm in diameter and porosity of over 75% (Fig. 8). By means of two alternative solvent systems—acetone and HFIP(1,1,1,3,3,3-hexafluoro-2-propanol) for electro-spinning supplied different results in

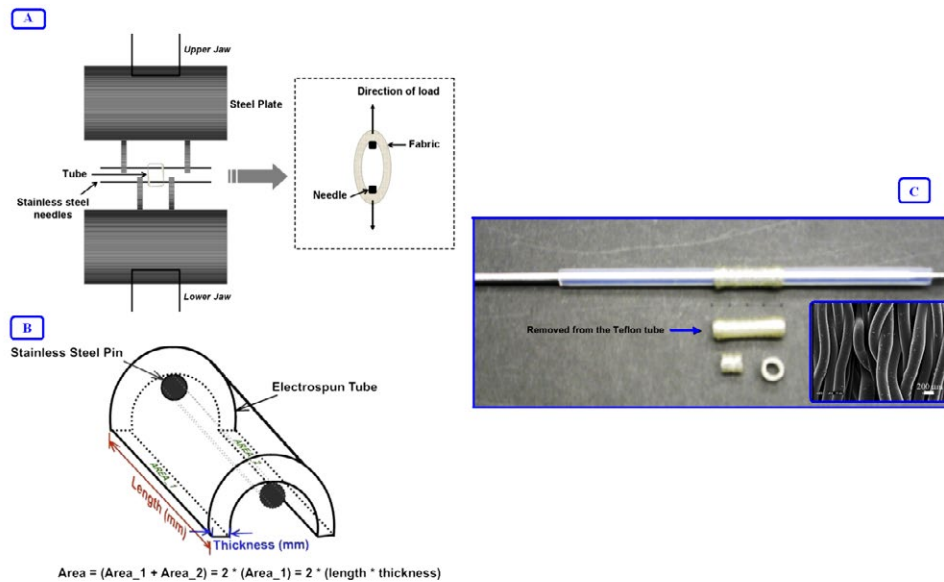


Fig. 8. (A) Commissioned holding border , (B) diagram presentation area-calculation , (C) Macroscopic appearance and SEM photomicrograph of the melt-spun PLCL tubes[52].

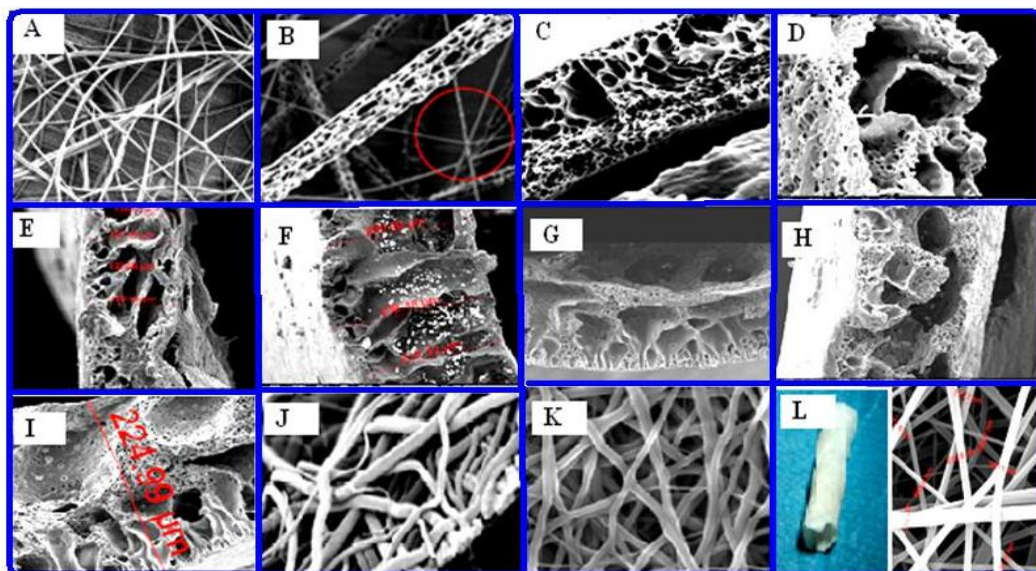


Fig. 9. SEM images of different PLA scaffolds for vascular tissue engineering; A) PLLA-CS (1:3) scaffolds; B) PLLA-CS (1:1) scaffolds; C) PLLA-PLA 90-10 tubular scaffolds prepared from a 8% wt polymer-dioxane solution at extraction rate of 20 cm/min; D) PLLA-PLA 90-10 tubular scaffolds prepared from a 8% wt polymer-dioxane solution at extraction rate of 30 cm/min; E) PLLA-PLA 90-10 tubular scaffolds prepared from a 10% wt polymer-dioxane solution at extraction rate of 15 cm/min; F) PLLA-PLA 90-10 tubular scaffolds prepared from a 10% wt polymer-dioxane solution at extraction rate of 20 cm/min; G) PLLA-PLA 75-25 tubular scaffolds prepared from a 10% wt polymer-dioxane solution at extraction rate of 30 cm/min; H) PLLA-PLA 75-25 tubular scaffolds; I) PLLA-PLA 75-25 tubular scaffolds prepared from a 10% wt polymer-dioxane solution at extraction rate of 40 cm/min; J) Bilyered PLA-PCL scaffolds , K) SF-P(LLA-CL) 0:100 scaffolds; L) Tubular PHEA-PLA-PCL scaffold [8, 19, 35, 52, 64].

fiber dimensions, mechanical properties and cytotoxicity, but the HFIP solvent was ideal because it gave a more stable thread line. The mechanical properties of both types of tubes revealed greater strength and compliance than natural arteries of equivalent caliber. Results showed that these two systems can be combined to fabricate double-layered tubular scaffolds holding both melt-spun macro-fibers (<200 μm in diameter) and electro-spun submicron-fibers (>400 nm in diameter) [52].

Pitarresi et. al.[8] electro-spun a mixture of PCL and α , ω -poly(N-2-hydroxyethyl) (2-aminoethyl-carbamate)-D,L-aspartamide-graft-Poly(lactic acid) (PHEA-EDA-g-PLA) as scaffold for blood-vessel regeneration. PHEA-EDA-g-PLA functional groups were utilized to covalently bond a considerable quantity of heparin (36 μg per mg of scaffold) which has been occupied to organize the release of fibroblast growth factor. Results reveal that the existence of both heparin and growth factor controls the capability of endothelial cells cultured in vitro upon the scaffold to create an integral endothelial layer[8].

P(LLA-CL)-Collagen-Chitosan 3-D nano-fibrous tubular scaffolds electro-spun for vascular grafts, in vitro examinations performed with culturing ECs cells days on scaffolds. Results illustrated that ECs

cells have good adhesion and proliferation on P(LLA-CL)-Collagen-Chitosan scaffolds compared to pure P(LLA-CL)[2]. A dual-porosity PLLA scaffold was developed for blood-vessel invasion. The nano-sized platelets were combined with PLLA solution, which was successively electro-spun and mechanically entangled by a cold compression molding procedure for a 3D scaffold[101].

Small diameter blood-vessel manufactured from Poly(l-lactic acid)-co-poly (ϵ -caprolactone) P(LLACL 70:30) (3 mm inner diameter) had mechanical assets nearer to that of native abdominal aorta. For instance, P(LLACL) nano-fibrous scaffold exhibited tensile strength of 3.9 ± 0.3 MPa in the circumferential direction, whilst the native abdominal aorta illustrated tensile strength of 5.29 MPa in the similar way. Also the scaffold approximately kept its integrity equipped 3 month in PBS solution at 37 $^{\circ}\text{C}$. Collagen coated P(LLACL) nano-fibrous scaffold via air plasma treatment aided adhesion, spread, and proliferation of Human coronary artery endothelial cells (HCAECs) after 10 days of culturing[2].

SEM Observation

Fig. 9 demonstrates SEM images of different PLA scaffolds for vascular tissue engineering that

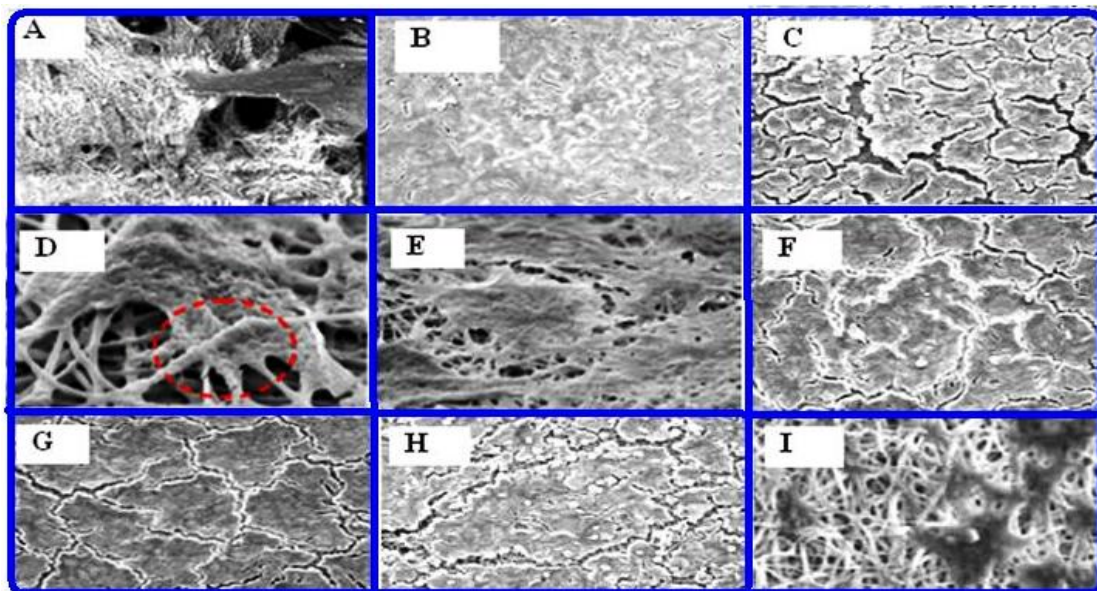


Fig.10. SEM images of different cells cultured on the PLA scaffolds: A) 3T3 mouse fibroblasts cells cultured on PCL-PLA nano-fibrous scaffold after 4 weeks. B) HCEC-B4G12 cells cultured on SF-P(LLA-CL) 100:0 nano-fibrous membrane after 1 week. C) Cells cultured on PLLA-CS after 1 day. D) Cells cultured on PLLA-CS after 7 days. E) Cells cultured on the PLLA-PLA scaffold after 14 days. F) HCEC-B4G12 cells cultured on SF-P(LLA-CL) 50:50 nano-fibrous scaffolds after 1 week. G) HCEC-B4G12 cells cultured on SF-P(LLA-CL) 25:75 nano-fibrous scaffolds after 1 week. H) HCEC-B4G12 cells cultured on SF-P(LLA-CL) 0:100 nano-fibrous scaffolds after 1 week. I) NIH 3T3 fibroblast cells (ATCC) cell attachment on PLCL scaffolds after 7 days of culture [14, 19, 35, 52, 64].

Table 3. Cytotoxicity and Cell Viability on PLA Vascular Scaffolds.

Type of Scaffold	Type of Cells	Unit of Cell Viability	Cell Viability (According to number of the days)								Cytotoxicity (%)	Ref.
			2 Hours	1 Day	2 Days	3 Days	4 Days	7 Days	14 Days	49 Days		
PLLA	UE7T—13	% (MTT assay)	—	0.6	—	—	0.62	0.7	—	—	—	[35]
PLLA—CS	UE7T—13	% (MTT assay)	—	0.61	—	—	0.7	1	—	—	—	[35]
PLLA	HUVECS	Cell number	—	—	120	—	—	—	—	—	—	[65]
PLLA + COII	HUVECS	Cell number	—	—	160	—	—	—	—	—	—	[65]
PLLA PdE: N	HUVECS	Cell number	—	—	180	—	—	—	—	—	—	[65]
PLLA PdE: N+ COII	HUVECS	Cell number	—	—	80	—	—	—	—	—	—	[65]
PLLA PdE:NH2	HUVECS	Cell number	—	—	70	—	—	—	—	—	—	[65]
PLLA PdE:NH2 + COII	HUVECS	Cell number	—	—	65	—	—	—	—	—	—	[65]
P(LLA—CA)—SF (8% w/v) 0:100	HCEC	OD 490 nm	—	0.35	—	—	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 25:75	HCEC	OD 490 nm	—	0.32	—	—	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 50:50	HCEC	OD 490 nm	—	0.5	—	—	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 75:25	HCEC	OD 490 nm	—	0.65	—	—	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 100: 0	HCEC	OD 490 nm	—	0.62	—	—	—	—	—	—	—	[19]
Electro—spun PLCL (Solvent : Acetone)	NIH 3T3 fibroblast	Absorbance, 550 nm (WST Assay)	—	0.77	—	0.07	—	0.1	0.63	—	—	[52]
Electro—spun PLCL (Solvent : HFIP)	NIH 3T3 fibroblast	Absorbance, 550 nm (WST Assay)	—	0.4	—	0.2	—	0.1	0.21	—	—	[52]
PLA— Fibrinogen (Random nano—fibers)	HUVECS	OD 490 nm	—	—	—	—	—	0.9	—	—	—	[14]
PLA— Fibrinogen (Aligned nano—fibers)	HUVECS	OD 490 nm	—	—	—	—	—	0.85	—	—	—	[14]
PLCL	SMCs	Cell number	—	—	—	—	—	—	—	11×10 ⁵	—	[97]
PLA	BHK—21	—	—	—	—	—	—	—	—	—	154.3±11.7	[98]
PLA + 1% wt CDPS	BHK—21	—	—	—	—	—	—	—	—	—	173.7±13.5	[98]
PLA + 3% wt CDPS	BHK—21	—	—	—	—	—	—	—	—	—	193.8±14.2	[98]
PLA + 5% wt CDPS	BHK—21	—	—	—	—	—	—	—	—	—	209.6±15.7	[98]
PLA + 7% wt CDPS	BHK—21	—	—	—	—	—	—	—	—	—	214.6±13.4	[98]
PLA + 9% wt CDPS	BHK—21	—	—	—	—	—	—	—	—	—	100.0±3.8	[98]
PLA—Collagen	Macrophages J774	Cell number	—	120	—	—	—	—	—	—	—	[102]
PLA—graft—Maleic Anhydride/Collagen	Macrophages J774	Cell number	—	520	—	—	—	—	—	—	—	[102]
PLCL	Red Blood Cells	Absorbance, 570 nm (MTT Assay)	0.043 ± 0.002	—	—	—	—	—	—	—	—	[94]
PCL80	Red Blood Cells	Absorbance, 570 nm (MTT Assay)	0.078±0.01	—	—	—	—	—	—	—	—	[94]
PCL45 22%	Red Blood Cells	Absorbance, 570 nm (MTT Assay)	0.065±0.02	—	—	—	—	—	—	—	—	[94]
PCL45 16%	Red Blood Cells	Absorbance, 570 nm (MTT Assay)	0.081 ± 0.010	—	—	—	—	—	—	—	—	[94]

HUVECS : Human umbilical vein endothelial cells; HCEC : human corneal endothelial cells; SMCs : Smooth muscle cells; OD : Optical Density; WST : Water Soluble Tetra—Zolium Salt;

reviewed above and Fig. 10 illustrates the SEM images of different cells cultured on PLA scaffolds for vascular regeneration.

CONCLUSIONS

Vascular defects and damages are the utmost

significant medical trouble and PLA scaffolds can be thought as a proficient key for this difficulty and support vascular regeneration. PLA bio-polymer has captured the most interest amongst the bio-degradable polymers as a tissue engineering material as PLA is easily process-able and degrades



Table 4. Comparison the Mechanical Properties of PLA Scaffolds with Some Natural Native Human Blood-vessels.

Type	Transverse Tensile Breaking Properties						Ref.
	Ultimate Stress (MPa)	Strain at Failure (%)	Elastic Modulus (MPa)	Burst Strength (mmHg)	Estimated Compliance (ml mm Hg ⁻¹)	Stiffness (N/m)	
Saphenous vein (circ.)	3	180	43	1680–3900	NA	NA	[2]
Saphenous vein (long.)	13	83	130	NA	NA	NA	[2]
Left internal mammary artery (circ.)	4.1	134	8	2000	NA	NA	[2]
Left internal mammary artery (long.)	4.3	59	16.8	NA	NA	NA	[2]
Femoral artery (circ.)	1–2	63–76	9–12	NA	NA	NA	[2]
Native Rabbit Aorta	2.61±0.4	86.7	—	1647±201	—	—	[2]
Melt—spun PLCL tubes	—	—	23.5 ± 0.9	—	0.0159	—	[52]
Electro—spun PLCL using acetone	—	—	24.6 ± 1.9	—	0.052	—	[52]
Electro—spun PLCL using HFIP	—	—	9.34 ±0.59	—	0.053	—	[52]
P(LLA—CA)—SF (8% w/v) 0:100	1.90±0.75	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 25:75	2.39±0.22	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 50:50	5.29±0.66	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 75:25	9.39±0.69	—	—	—	—	—	[19]
P(LLA—CA)—SF (8% w/v) 100: 0	7.47±0.38	—	—	—	—	—	[19]
PLCL	1.91±0.56	135	—	604±4	—	—	[97]
PLLA	1.5	—	65	—	—	—	[35]
PLLA—CS	3	—	115	—	—	—	[35]
PLA—PCL	4.3 ± 0.2	47.0 ±6.3	30.9 ± 6.6	—	—	—	[2]
PLLACL coated with collagen	3.9 ± 0.3	—	16.6 ± 4.4	—	—	—	[2]
PLA	—	—	—	—	—	8000	[14]
PLA—Fibrinogen	—	—	—	—	—	500	[14]
Fibrinogen	—	—	—	—	—	50	[14]
PLA	0.55	34	—	—	—	—	[98]
PLA + 1% wt CDPS	0.575	35	—	—	—	—	[98]
PLA + 3% wt CDPS	0.56	33	—	—	—	—	[98]
PLA + 5% wt CDPS	0.58	35	—	—	—	—	[98]
PLA + 7% wt CDPS	0.59	39	—	—	—	—	[98]
PLA + 9% wt CDPS	0.62	37.5	—	—	—	—	[98]
PLA	3.5	180	75	—	—	—	[102]
Collagen	0.75	20	25	—	—	—	[102]
PLA—Collagen	2.2	70	30	—	—	—	[102]
PLA—graft—Maleic Anhydride/Collagen	3.1	120	73	—	—	—	[102]
PLA—PGA	—	—	3	—	—	—	[62]
PLA—SF—Gel	2.21 ± 0.18	60.58 ± 1.23	—	1596±20	—	—	[24]

*Circ: circumferential; long: longitudinal; NA: not available; Ref: Reference number.

and disintegrates into natural metabolites while matching its degradation rate with the healing time of damaged human tissues. Therefore, this paper reviewed the potential of PLA scaffolds to favor vascular tissue engineering owing to its biological care and tunable degradation structures. At last,

the authors suggest different approach “UV/Ozone Irradiation” for surface functionalization of PLA scaffolds so as to development the vascular cell adhesion, differentiation and proliferation. This approach is predictable to increase the success of vascular regeneration.

Table 5. Basic features of the PLA vascular scaffolds.

Type of PLA scaffold	Nano—fiber diameter (nm)	Specimen Thickness	Contact Angle (Degrees)	Tg (°C)	Tm (°C)	Ref.*	
P(LLA—CA)—SF (8% w/v) 0:100	Nano—fibrous	147±24	30±9.53 μm	38.36±0.41 (at 20 seconds)	—	—	[19]
P(LLA—CA)—SF (8% w/v) 25:75	Nano—fibrous	226±31	56±5.12 μm	49.03±0.67 (at 20 seconds)	—	—	[19]
P(LLA—CA)—SF (8% w/v) 50:50	Nano—fibrous	255±37	62.5±7.93 μm	62.93±0.50 (at 20 seconds)	—	—	[19]
P(LLA—CA)—SF (8% w/v) 75:25	Nano—fibrous	226±24	56±4.20 μm	71.58±0.15 (at 20 seconds)	—	—	[19]
P(LLA—CA)—SF (8% w/v) 100: 0	Nano—fibrous	542±107	128±6.65 μm	125.78±0.02 (at 20 seconds)	—	—	[19]
PLA—Fibrinogen (Random)	Nano—fibrous	400	—	—	—	—	[14]
PLA—Fibrinogen (Aligned)	Nano—fibrous	250	—	—	—	—	[14]
PLA—CS—HLC	Nano—fibrous	148	—	—	—	—	[30]
PLLA—PLA 90:10	Tubular	—	180 μm	—	—	—	[64]
PLLA—PLA 75:25	Tubular	—	165 μm	—	—	—	[64]
Air—Spun PLA Nano—fibers	Nano—fibrous	—	—	110 (at 20 seconds)	—	—	[18]
Air—Spun PLA Nano—fibers	Nano—fibrous	—	—	80 (at 40 seconds)	—	—	[18]
Air—Spun PLA Nano—fibers	Nano—fibrous	—	—	45 (at 60 seconds)	—	—	[18]
Air—Spun PLA Nano—fibers	Nano—fibrous	—	—	10 (at 80 seconds)	—	—	[18]
Electro—spun PLCL Tubes (Solvent : Acetone)	Tubular	—	0.033 mm	—	—	—	[52]
Electro—spun PLCL Tubes (Solvent : HFIP)	Tubular	—	0.118 mm	—	—	—	[52]
PLA—graft—Maleic Anhydride	Nano—fibrous	—	—	—	52.11	148.71	[102]
PLA—graft—Maleic Anhydride : Collagen 30:1	Nano—fibrous	450	—	—	61.82	152.3	[102]
PLA—graft—Maleic Anhydride : Collagen 15:1	Nano—fibrous	650	—	—	61.73	152.51	[102]
PLA—Col	Nano—fibrous	500	—	—	60.44	151.75	[102]
PLA	Nano—fibrous	100	—	—	60.36	151.75	[102]
PLCL	Nano—fibrous	1100	—	—	—	—	[94]
PCL80	Nano—fibrous	860	—	—	—	—	[94]
PCL45 22%	Nano—fibrous	470	—	—	—	—	[94]
PCL45 16%	Nano—fibrous	300	—	—	—	—	[94]

HFIP : 1,1,1,3,3,3—Hexafluoro—2—Propanol

CONFLICT OF INTEREST

The author declares no conflict of interest.

REFERENCES

- Ye K, Kuang H, You Z, Morsi Y, Mo X. Electrospun Nanofibers for Tissue Engineering with Drug Loading and Release. *Pharmaceutics*, 2019;11.
- Awad NK, Niu H, Ali U, Morsi YS, 2 TL. Electrospun Fibrous Scaffolds for Small-Diameter Blood Vessels: A Review. *Membranes*, 2018;8 (15).
- Daly AC, Pitacco P, Nulty J, Cunniffe GM, DJ. K. 3D printed microchannel networks to direct vascularisation during endochondral bone repair. *Biomaterials*, 2018;162 (57):34-46.
- Ercolani E, Del Gaudio C, Bianco A. Vascular tissue engineering of small-diameter blood vessels: reviewing the electrospinning approach. *Journal of Tissue Engineering and Regenerative Medicine*, 2015;9 (8):861-888.
- Kong B, Mi S. Electrospun Scaffolds for Corneal Tissue Engineering: A Review. *Materials*, 2016;9:614-634.
- Alida Abruzzo, Calogero Fiorica, Vincenzo Davide Palumbo, Roberta Altomare, Giuseppe Damiano, Maria Concetta Gioviale, Giovanni Tomasello, Mariano Licciardi, Fabio Salvatore Palumbo, Gaetano Giammona, Monte AIL. Using Polymeric Scaffolds for Vascular Tissue Engineering. *International Journal of Polymer Science*, 2014.
- Gu Y-q, Wang Z, Sun Y, Wang Y-K, Pan Z-j. Micro-scale PLA Fibrous Membranes for Adsorption of Cigarette Smoke. *Fibers and Polymers*, 2018;19 (3):515-523.
- G. Pitarresi, C. Fiorica, F. S. Palumbo, S. Rigogliuso, G. Ghersi, G. Giammona. Heparin functionalized polyaspartamide/polyester scaffold for potential blood vessel regeneration., *Journal of Biomedical Materials ResearchA*, 2014;102 (5):1334-1341.
- Ding G-R, Li K-C, Wang X-W, Zhou Y-C, Qiu L-B, Tan J, Xu S-L, Guo G-Z. Effect of Electromagnetic Pulse Exposure on Brain Micro Vascular Permeability in Rats. *Biomedical and Environmental Sciences*, 2009;22 (3):265-268.
- H. E. Burton, J. M. Freij, Espino DM. Dynamic viscoelasticity and surface properties of porcine left anterior descending



- coronary arteries. *Cardiovascular Engineering and Technology*, 2017;8 (1):41–56.
11. van der Slegt J, Steunenberg SL, Donker JM. The current position of precuffed expanded polytetrafluoroethylene bypass grafts in peripheral vascular surgery. *J Vasc Surg*, 2014;60:120–128.
 12. Burton HE, Espino DM. The Effect of Mechanical Overloading on Surface Roughness of the Coronary Arteries. *Applied Bionics and Biomechanics*, 2019.
 13. Krawiec JT, DA. V. Adult stem cell-based tissue engineered blood vessels: a review. *Biomaterials*, 2012;33:3388–3400.
 14. Gugutkov D, Gustavsson J, Cantini M, Salmeron-Sánchez M, Altankov G. Electrospun fibrinogen–PLA nanofibres for vascular tissue engineering. *Journal of Tissue Engineering and Regenerative Medicine*, 2017;11 (10):2774–2784.
 15. Zhang C, Wen J, Yan J, Kao Y, Ni Z, Cui X, Wang H. In situ growth induction of the corneal stroma cells using uniaxially aligned composite fibrous scaffolds. *RSC Adv*, 2015;5:12123–12130.
 16. Riegler J. Superparamagnetic iron oxide nanoparticle targeting of MSCs in vascular injury. *Biomaterials*, 2013;34:1987–1994.
 17. Hai Wang, Xiao Chang, Guixing Qiu, Fuzhai Cui, XishengWeng, Baozhong Zhang, Xiaojie Lian, Wu Z. Vascularization of Nanohydroxyapatite/Collagen/Poly(L-lactic acid) Composites by Implanting Intramuscularly In Vivo. *International Journal of Polymer Science*, 2014; .
 18. Na Re Ko , Gad Sabbatini , Alexander Cunningham , Gaétan Laroche , . JKO. Air-Spun PLA Nanofibers Modified with Reductively Sheddable Hydrophilic Surfaces for Vascular Tissue Engineering: Synthesis and Surface Modification. *Macromol Rapid Commun*, 2014;35:447–453.
 19. Chen J, Yan C, Zhu M, Yao Q, Shao C, Lu W, Wang J, Mo X, Gu P, Fu Y, Fan X. Electrospun nanofibrous SF/P(LLA-CL) membrane: a potential substratum for endothelial keratoplasty. *International Journal of Nanomedicine*, 2015;10:3337–3350.
 20. Greenwald SE, CL. B. Improving vascular grafts: the importance of mechanical and haemodynamic properties. *J Pathol*, 2000;190:292–299.
 21. Thottappillil N, Nair PD. Scaffolds in vascular regeneration: current status. *Vascular Health and Risk Management*, 2015;11:79–91.
 22. Hussain A, Collins G, Yip D, CH C. Functional 3-D cardiac co-culture model using bioactive chitosan nanofiber scaffolds. *Biotechnology and Bioengineering*, 2013;110 (2):637–647.
 23. Shalomon KT, Chennazhi KP, Anupama MS, Jayakumar R, Deepthi S, Nair SV. Fabrication of poly (l-lactic acid)/gelatin composite tubular scaffolds for vascular tissue engineering. *International journal of biological macromolecules*, 2015;9.
 24. Wang Z, Cui Y, Wang J, Yang X, Wu Y, Wang K, Gao X, Li D, Li Y, Zheng X-L. The effect of thick fibers and large pores of electrospun poly(ε-caprolactone) vascular grafts on macrophage polarization and arterial regeneration. *Biomaterials* 2014;35:5700–5710.
 25. Wang Y, Hu J, Jiao J, Liu Z, Zhou Z, Zhao C, Chang LJ, Chen YE, Ma PX, B Y. Engineering vascular tissue with functional smooth muscle cells derived from human iPS cells and nanofibrous scaffolds. *biomaterials*, 2014;35 (32):8960–8969.
 26. Xiao Chang, Hai Wang, ZhihongWu, Xiaojie Lian, Fuzhai Cui, XishengWeng, Bo Yang, Guixing Qiu, Zhang1 B. Enhancement of VEGF on Axial Vascularization of Nano-HA/Collagen/PLA Composites: A Histomorphometric Study on Rabbits. *International Journal of Polymer Science*, 2014.
 27. Zhang E, F S. Blood compatibility of a ferulic acid (FA)-eluting PHBHHx system for biodegradable magnesium stent application. *Mater Sci Eng C Mater Biol Appl*, 2015;52:37–45.
 28. Khan M, Xu Y, Hua S, Johnson J, Belevych A, Janssen PML, Gyorko S, Guan J, MG A. Evaluation of changes in morphology and function of human induced pluripotent stem cell derived cardiomyocytes (HiPSC-CMs) cultured on an aligned-nanofiber cardiac patch. *PLOS ONE*, 2015;10 (5).
 29. Qiang Shi, Jianwen Hou, Chunyu Zhao, Xin Z, Jing Jin, Chunming Li, Wong S-C, Yin J. A Smart Core-sheath Nanofiber that Captures and Releases Red Blood Cells from the Blood. *The Royal Society of Chemistry*, 2015.
 30. Zhu C, Ma X, Xian L, Zhou Y, Fan D. Characterization of a co-electrospun scaffold of HLC/CS/PLA for vascular tissue engineering. *Bio-Medical Materials and Engineering*, 2014;24.
 31. Zhang E, Chen H, F. S. Biocorrosion properties and blood and cell compatibility of pure iron as a biodegradable biomaterial. *J Mater Sci Mater Med*, 2010;21 (7):2151–2163.
 32. Wang J, An Q, Li D, Wu T, Chen W, Sun B, El-Hamshary H, Al-Deyab SS, Zhu W, Mo X. Heparin and vascular endothelial growth factor loaded poly(l-lactide-co-caprolactone) nanofiber covered stent-graft for aneurysm treatment. *J Biomed Nanotechnol*, 2015;11:1947–1960.
 33. Mazalevska O, Struszczyk MH, Krucinska I. Design of vascular prostheses by melt electrospinning— Structural characterizations. *J Appl Polym Sci*, 2013;129:779–792.
 34. E.C. Chan, S.-M. Kuo, A.M. Kong, W.A. Morrison, G.J. Dusting, Mitchell GM. Three dimensional collagen scaffold promotes intrinsic vascularisation for tissue engineering applications. *PloS One*, 2016;11.
 35. Ting Wang, Xuyuan Ji, Lin Jin, Zhangqi Feng, Jinghang Wu, Jie Zheng, | Hongyin Wang, Zhe-Wu Xu, Lingling Guo, He N. Fabrication and Characterization of Heparin-Grafted Poly(L-lactic acid)–Chitosan Core–Shell Nanofibers Scaffold for Vascular Gasket. *Appl Mater Interfaces*, 2013;5:3757–3763.
 36. Zhu Y, Leong MF, Ong WF, Chan-Park MB, KS. C. Esophageal epithelium regeneration on fibronectin grafted poly(L-lactide-co-caprolactone) (PLL) nanofiber scaffold. *Biomaterials*, 2007;28:861–868.
 37. Thottappillil N, Nair PD. Scaffolds in vascular regeneration:current status. *Vascular Health and Risk Management*, 2015;11:79–91.
 38. Jing X, Mi H-Y, Salick MR, Cordie TM, Peng X-F, Turng L-S. Electrospinning thermoplastic polyurethane/graphene oxide scaffolds for small diameter vascular graft applications. *Materials Science and Engineering: C*, 2015;49:40–50.
 39. Sankaran KK, Vasanthan KS, Krishnan UM, S S. Development and evaluation of axially aligned nanofibres for blood vessel tissue engineering: small-diameter aligned nanofibrous vascular graft. *Journal of Tissue Engineering and Regenerative Medicine*, 2014;8 (8):640–651.
 40. Vaz C, Van Tuijl S, Bouten C, Baaijens F. Design of scaffolds for blood vessel tissue engineering using a multi-layering electrospinning technique. *Acta Biomater*, 2005;1:575–582.
 41. Namdee K, Thompson AJ, Charoenphol P, Eniola-Adefeso O. Margination Propensity of Vascular-Targeted Spheres from Blood Flow in a Microfluidic Model of Human Microvessels. *Langmuir*, 2013;29:2530–2535.
 42. Y. Pang, Greisler HP. Using a type I collagen based system to understand cell-scaffold interactions and to deliver chimeric collagen binding growth factors for vascular tissue engineering. *J Investig Med Off Publ Am Fed Clin Res*, 2010;58.
 43. Stegemann JP, Kaszuba SN, SL. R. Review: advances in vascular tissue engineering using protein-based biomaterials.

- . Tissue Eng, 2007;13:2601–2613.
44. Pieper S, Onafuye H, Mulac D, jr JC, Wass MN, Michaelis M, K.Langer. Incorporation of doxorubicin in different polymer nanoparticles and their anti-cancer activity. 2018.
 45. Y. Pang, Greisler HP. Using a type I collagen based system to understand cell-scaffold interactions and to deliver chimeric collagen binding growth factors for vascular tissue engineering. J Investig Med Off Publ Am Fed Clin Res, 2011;58.
 46. Hu Z jun, Li Z lun, Hu L yu, He W, Liu R ming, Qin Y sen, ming. WS. The in vivo performance of small-caliber nanofibrous polyurethane vascular grafts. BMC Cardiovascular Disorders, 2012;12 (1).
 47. Drews JD, Miyachi H, Shinoka T. Tissue-engineered vascular grafts for congenital cardiac disease: Clinical experience and current status. Trends Cardiovasc Med, 2017;27:521–531.
 48. Sugiura T, Matsumura G, Miyamoto S, Miyachi H, Breuer CK, Shinoka T. Tissue-engineered Vascular Grafts in Children With Congenital Heart Disease: Intermediate Term Follow-up. Semin Thoracic Surg, 2018;30:175–179.
 49. Ruiz-Rosado, J.D.; Mahler, N.; Yi T, Robledo AF, Martinez SD, Lee AY, Shoji T, Lee AY, Heuer E, Yates AR. Angiotensin II receptor I blockade prevents stenosis of tissue engineered vascular grafts. FASEB J, 2018;15.
 50. Santoro M, Shah SR, Walker JL, Mikos AG. Poly(lactic acid) nanofibrous scaffolds for tissue engineering. Advanced Drug Delivery Reviews, 2016;107:206-212.
 51. Ju YM, Choi JS, Atala A, Yoo JJ, SJ. L. Bilayered scaffold for engineering cellularized blood vessels. Biomaterials, 2010;31:4313–4321.
 52. Chung S, Ingle NP, Montero GA, Kim SH, King MW. Bioresorbable elastomeric vascular tissue engineering scaffolds via melt spinning and electrospinning. Acta Biomaterialia, 2010.
 53. N.B. Shelke, R. Kadam, P. Tyagi, V.R. Rao, Kompella UB. Intravitreal poly(lactide) microparticles sustain retinal and choroidal delivery of TG-0054, a hydrophilic drug intended for neovascular diseases. Drug Deliv Transl Res, 2011;1.
 54. Kucinska-Lipka J, Gubanska I, Janik H, Sienkiewicz M. Fabrication of polyurethane and polyurethane based composite fibres by the electrospinning technique for soft tissue engineering of cardiovascular system. Materials Science and Engineering: C, 2015;46:166-176.
 55. Wang S, Zhang Y, Wang H, Yin G, Dong Z. Fabrication and properties of the electrospun poly(lactide)/silk fibroin-gelatin composite tubular scaffold. Biomacromolecules, 2009;10:2240–2244.
 56. Gebremariam Birhanu, Shima Tanha, Hamid Akbari Javar, Ehsan Seyedjafari, Zandi-Karimi A, Dehkordi BK. Dexamethasone loaded multi-layer poly-L-lactic acid/pluronic P123 composite electrospun nanofiber scaffolds for bone tissue engineering and drug delivery. Pharmaceutical Development and Technology, 2018.
 57. AM. P. Electrospun Type 1 collagen matrices using a novel benign solvent for cardiac tissue engineering. Journal of Cellular Physiology, 2016;231 (3).
 58. Feng W, Liu P, Yin H, Gu Z, Wu Y, Zhu W, Liu Y, Zheng H, Mo X. Heparin and rosuvastatin calcium loaded poly(L-lactide-co-caprolactone) nanofiber covered stent-graft for aneurysm treatment. New J Chem, 2017;41:9014–9023.
 59. Fattahi FS, Khoddami A, Izadian H. Review on Production, Properties, and Applications of Poly(lactic acid) Fibers. Journal of Textile Science and Technology, 2015;5 (1):11-17.
 60. Kiran Kumar Cherreddy, Alessandra Lopes, Salome Koussoroplis, Valéry Payen, Claudia Moia, Huijun Zhu, Pierre Sonveaux, Peter Carmeliet, Anne des Rieux, Gaëlle Vandermeulen, Véronique Pr at. Combined effects of PLGA and vascular endothelial growth factor promote the healing of non-diabetic and diabetic wounds. Nanomedicine: Nanotechnology, Biology, and Medicine, 2015;11:1975–1984.
 61. Yin A, Bowlin GL, Luo R, Zhang X, Wang Y, Mo X. Electrospun silk fibroin/poly(L-lactide- -caplacton) graft with platelet-rich growth factor for inducing smooth muscle cell growth and infiltration. Regen Biomater, 2016;3:239-245.
 62. Meng Deng, Yunpeng Gu, Zhenjun Liu, Yue Qi, Gui E. Ma, Kang N. Endothelial Differentiation of Human Adipose-Derived Stem Cells on Polyglycolic Acid/Polylactic Acid Mesh. Stem Cells International, 2015.
 63. Qasim M, Chae DS, Lee NY. Advancements and frontiers in nano-based 3D and 4D scaffolds for bone and cartilage tissue engineering. International Journal of Nanomedicine, 2019;14:4333–4351.
 64. Pavia FC, Rigogliuso S, Carrubba VL, Mannella GA, Ghersi G, Brucato V. Poly Lactic Acid Based Scaffolds for Vascular Tissue Engineering. CHEMICAL ENGINEERING TRANSACTIONS, 2012;27.
 65. Salvatrice Rigogliuso, Francesco Carfi Pavia, Valerio Brucato, Vincenzo La Carrubba, Pietro Favia, Francesca Intranuovo, Roberto Gristina, Ghersi G. Use of Modified 3D Scaffolds to Improve Cell Adhesion and Drive Desired Cell Responses. CHEMICAL ENGINEERING TRANSACTIONS, 2012;27.
 66. Fattahi F, Izadan H, Khoddami A. Investigation into the Effect of UV/Ozone Irradiation on Dyeing Behaviour of Poly(Lactic Acid) and Poly(Ethylene Terephthalate) Substrates. Prog Color Colorants Coat, 2012;5:15-22.
 67. Nofar M, Sacligil D, Carreau PJ, Kamal MR, Heuzey M-C. Poly (lactic acid) blends: Processing, properties and applications. International Journal of Biological Macromolecules, 2019;125:307-360.
 68. Iulian, Popescu D, Zapciu A, Antoniac A, Miculescu F, Moldovan H. Magnesium Filled Polylactic Acid (PLA) Material for Filament Based 3D Printing. Materials 2019;12 (719).
 69. Fattahi FS, Khoddami A, Izadan H. A Review on Poly(lactic acid) Textile Goods Finishing: Plasma Treatment, UV/Ozone Irradiation, Superhydrophobic Surface Manufacturing and Enzymatic Treatment. Journal of Apparel and Textile Science and Technology, 2017(2):19-26.
 70. Fattahi F-s, Khoddami A, Avinc O. Poly(lactic acid) (PLA) Nanofibers for Bone Tissue Engineering. JOURNAL OF TEXTILES AND POLYMERS, 2019;7 (2):47-64.
 71. Avinc o, Khoddami A. Overview of Poly(Lactic Acid) (PLA) Fibre Part II: Wet Processing; Pretreatment, Dyeing, Clearing, Finishing, and Washing Properties of Poly(lactic acid) Fibres. Fibre Chem, 2010;1:68-78.
 72. Alves PE, Soares BG, Lins LC, Livi S, Santos EP. Controlled delivery of dexamethasone and betamethasone from PLA electrospun fibers: A comparative study. European Polymer Journal, 2019.
 73. Lertphirun K, Srikulkit K. Properties of Poly(Lactic Acid) Filled with Hydrophobic Cellulose/SiO2 Composites. International Journal of Polymer Science, 2019.
 74. Mohiti-Asli M, Saha S, Murphy SV, Gracz H, Pourdeyhimi B, Alqtish A, Lobo E. Ibuprofen loaded PLA nanofibrous scaffolds increase proliferation of human skin cells in vitro and promote healing of full thickness incision wounds in vivo;

- 2015.
75. Thi Thu Trang Mai, Thi Thu Thuy Nguyen, Le QD, Nguyen TN, Ba TC, Nguyen HB, Phan TBH, Tran DL, Nguyen XP, Park JS. A novel nanofiber Cur-loaded polylactic acid constructed by electrospinning. *Adv Nat Sci: Nanosci Nanotechnol*, 2012;3.
 76. Khan AuR, Xiangyang S, Ahmad A, Mo X-m. Electrospinning of Crude Plant Extracts for Antibacterial and Wound Healing Applications: A Review. *SM Journal of Biomedical Engineering*, 2018;4 (1).
 77. T G, T L, L Z, W Y, X G, L W. Design redox-sensitive drug-loaded nanofibers for bone reconstruction. *ACS Biomater Sci Eng*, 2018;4 (1):240–247 .
 78. Sadat Fattahi F, Khoddami A, O. A. Poly (Lactic Acid) Nano-fibers as Drug-delivery Systems: Opportunities and Challenges. *Nanomed Res J*, 2019;4 (3):130-140.
 79. Xu T, Yang H, Yang D, Yu Z-Z. Polylactic Acid Nanofiber Scaffold Decorated with Chitosan Islandlike Topography for Bone Tissue Engineering. *ACS Applied Materials & Interfaces*, 2017;9 (25):21094-21104.
 80. Yu F, Li M, Yuan Z, Rao F, Fang X, Jiang B, Wen Y, Zhang P. Mechanism research on a bioactive resveratrol- PLA-gelatin porous nano-scaffold in promoting the repair of cartilage defect. *International Journal of Nanomedicine*, 2018;13:7845–7858.
 81. Przekora A. Current Trends in Fabrication of Biomaterials for Bone and Cartilage Regeneration: Materials Modifications and Biophysical Stimulations. *Int J Mol Sci*, 2019;20 (435).
 82. Mohiti-Asli M, Saha S, Murphy SV, Gracz H, Pourdeyhimi B, Atala A, Lobo EG. Ibuprofen loaded PLA nanofibrous scaffolds increase proliferation of human skin cells in vitro and promote healing of full thickness incision wounds in vivo. *Journal of Biomedical Materials Research Part B: Applied Biomaterials*, 2017;105 (2):327-339.
 83. Tyler B, Gullotti D, Mangraviti A, Utsuki T, Brem H. Polylactic acid (PLA) controlled delivery carriers for biomedical applications. *Advanced Drug Delivery Reviews*, 2016;107:163-175.
 84. Mehdikhani M, Tavakoli E, Zargar-Kharazi A, Hashemibeni B. A novel nano-composite scaffold for cartilage tissue engineering. *Scientia Iranica*, 2018;25 (3):1815-1823.
 85. Wu C, An Q, Li D, Jing W, He L, Chen H, Yu L, Wei Z, Mo X. A novel heparin loaded poly(L-lactide-co-caprolactone) covered stent for aneurysm therapy. *Mater Lett*, 2014;116:39–42.
 86. Matsuzaki Y, John K, Shoji T, Shinoka T. The Evolution of Tissue Engineered Vascular Graft Technologies: From Preclinical Trials to Advancing Patient Care. *Appl Sci*, 2019;9.
 87. Castro-Aguirre E, Iñiguez-Franco F, Samsudin H, Fang X, Auras R. Poly(lactic acid)—Mass production, processing, industrial applications, and end of life. *Advanced Drug Delivery Reviews*, 2016;107:333-366.
 88. Basu A, Kunduru KR, Doppalapudi S, Domb AJ, Khan W. Poly(lactic acid) based hydrogels. *Advanced Drug Delivery Reviews*, 2016;107:192-205.
 89. Basu A, Kunduru KR, Katzhendler J, Domb AJ. Poly(α -hydroxy acids) and poly(α -hydroxy acid-co- α -amino acids) derived from amino acid. *Advanced Drug Delivery Reviews*, 2016;107:82-96.
 90. James R, Manoukian OS, Kumbar SG. Poly(lactic acid) for delivery of bioactive macromolecules. *Advanced Drug Delivery Reviews*, 2016;107:277-288.
 91. Fattahi F, Izadan H, Khoddami A. Deep Dyeing of Poly (lactic acid) and Poly (ethylene terephthalate) Fabrics Using UV/ Ozone Irradiation. 4th International Color and Coatings Congress (ICCC 2011) November 22-24, 2011 Tehran–Iran, 2011.
 92. Avinc o, Khoddami A. Overview of poly(lactic acid) (PLA) fibre part I: production, properties, performance, environmental impact, and end-use applications of poly(lactic acid) fibres. *Fibre Chem*, 2009;41:391-401.
 93. Farah S, Anderson DG, Langer R. Physical and mechanical properties of PLA, and their functions in widespread applications — A comprehensive review. *Advanced Drug Delivery Reviews*, 2016;107:367-392.
 94. Horakova J, Mikes P, Saman A, Svarcova T, Jencova V, Suchy T, Heczkova B, Jakubkova S, Jirouskova J, Prochazkova R. Comprehensive assessment of electrospun scaffolds hemocompatibility. *Materials Science and Engineering C*, 2018;82:330–335.
 95. Tara S, Kurobe H, Rocco KA, Maxfield MW, Best CAY, T; , Breuer CK, Shinoka T. Well-organized neointima of large-pore poly(L-lactic acid) vascular graft coated with poly(L-lactide-co- ϵ -caprolactone) prevents calcific deposition compared to small-pore electrospun poly(L-lactic acid) graft in a mouse aortic implantation model. *Atherosclerosis*, 2014;237:684–691.
 96. Shalumon KT, Chennazhi KP, Anupama MS, Jayakumar R, Deepthi S, Nair SV. Fabrication of poly (l-lactic acid)/gelatin composite tubular scaffolds for vascular tissue engineering. *International journal of biological macromolecules*, 2014;9.
 97. Mun CH, Jung Y, Kim S-H, Lee S-H, Kim HC, Kwon IK, Kim SH. Three-dimensional electrospun poly(lactide-co- ϵ -caprolactone) for small-diameter vascular grafts. *Tissue Eng Part A*, 2012;18:1608–1616.
 98. Zhang Weijie, Chen Zhuo, Ma Sujuan, Wang Yonggang, Zhang Fei, Wang Keyi, Yang Chenguang, Pu Xiuying, Ma Jianzhong, Wang Yuli, Leng Feifan, Fen R, Yanbei K. Cistanche polysaccharide (CDPS)/polylactic acid (PLA) scaffolds based coaxial electrospinning for vascular tissue engineering. *International Journal of Polymeric Materials and Polymeric Biomaterials*, 2016;65 (1):38-46.
 99. T.Wu BJ, Y.Wang, T.Wu, B. Jiang, Y.Wang, A. Yin, Ch. Huang, S.Wang, Mo X. Electrospun poly(L-lactide-co-caprolactone)-collagen-chitosan vascular graft in a canine femoral artery. *J Mater Chem* 2015;B 3:5760–5768.
 100. Montini Ballarin F, Caracciolo PC, Blotta E, Ballarin VL, Abraham GA. Optimization of poly(l-lactic acid)/segmented polyurethane electrospinning process for the production of bilayered small-diameter nanofibrous tubular structures. *Materials Science and Engineering: C*, 2014;42:489-499.
 101. Lee YH, Lee JH, An I-G, Kim C, Lee DS, Lee YK, Nam J-D. Electrospun dual-porosity structure and biodegradation morphology of Montmorillonite reinforced PLLA nanocomposite scaffolds. *Biomaterials*, 2005;26 (16):3165-3172.
 102. Ospina-Orejarena A, Vera-Graziano R, Castillo-Ortega MM, Hinestroza JP, Rodriguez-Gonzalez M, Palomares-Aguilera L, Morales-Moctezuma M, Maciel-Cerda A. Grafting Collagen on Poly (Lactic Acid) by a Simple Route to Produce Electrospun Scaffolds, and Their Cell Adhesion Evaluation. *Tissue Eng Regen Med*, 2016;13 (4):375-387.